EUROPEAN DATABASE FOR CORRUGATED BOARD LIFE CYCLE STUDIES 2025

REPORT PREPARED BY RISE BIOECONOMY ON BEHALF OF FEFCO AND CONTAINERBOARD EUROPE



CONTAINERBOARD EUROPE

FEFCO Corrugated Packaging

CONTENTS

FOREWORD **3**

DESCRIPTION OF THE PRODUCT SYSTEM **5**

Paper production process 5

Corrugated board production 7

Corrugated base papers and corrugated board 9

METHODOLOGY QUESTIONS **12**

Boundaries and declared unit 12

System boundaries for corrugated base papers 14

System boundaries for corrugated board and boxes 16

The closed-loop approach 18

Definitions and calculations of recovery and recycling 20

DATA DESCRIPTION **21**

Questionnaire / Data collection for corrugated base papers 21

Data collection for corrugated board and box production 21

Weighted averages 21

Material inputs 22

Material outputs 23

Energy input and output 24

Water inputs and outputs 25

Transport 25

Emissions to air 26

Emissions to water 28

DATA **30**

Coverage and comparability of the datasets over time 30

Relationship to the Product Environmental Footprint (PEF) 30

Results 32

Life cycle inventory for corrugated board 2024 32

Additional information on energy and fuels 38

Internal fuels 38

Sustainable forest management 39

PEER REVIEW **39**

DEFINITIONS **40**

ANNEX 1 **41**

ANNEX 2: PEER REVIEW STATEMENT **47**

FOREWORD

FEFCO (European Federation of Corrugated Board Manufacturers) and Containerboard Europe[1] regularly issue a report and database of gate-to-gate life cycle inventory data for the production of corrugated base papers and corrugated products. The intention is to make available high quality and transparent LCI data for use in life cycle studies.

Over the course of multiple iterations of the project a robust process has been developed in which the data provided is processed and checked by both LCA practitioners and industry experts. The process and data are then subjected to an independent peer review by Frank Wellenreuther of ifeu – Institute for Energy and Environmental Research Heidelberg gGmbH, Heidelberg, Germany – a leading research institution with experience of life cycle data and methods as applied in the paper and board sector.

The Annex of the report contains environmental data for the production of

- Corrugated base papers from primary fibres: kraftliner, white top kraftliner and semi chemical fluting (based on data supplied by members of Containerboard Europe)
- Corrugated base papers from recovered papers: testliner, white top testliner and recycled fluting (sometimes referred to as Wellenstoff) (based on data supplied by members of Containerboard Europe)
- Corrugated board products (based on data supplied by members of FEFCO).

The data in this twelfth edition of the report represents the weighted averages of the inputs and outputs from the production sites per tonne of paper and per tonne of corrugated board product for the year **2024**. The database handles the production sites as a black box. Details of the different processes in the production site are not provided. Emissions etc. originating from production of resources consumed, energy production outside the mill or corrugated plant, transport and waste treatment are not included in the datasets, but the impacts of these additional unit processes can be added by the user to facilitate full cradle-to-gate or cradle-to-cradle life cycle studies.

The data collected for this study covers a significant proportion of the sector. For semi chemical fluting and kraftliner, the collected data represents approximately 86% of the total annual production of corrugated base papers from primary fibres in Europe, whilst the data for the production of testliner (including white top testliner) and recycled fluting (wellenstoff) were collected from mills, together producing about 63% of the total annual production of corrugated base papers from recovered paper in Europe. Data for corrugated board production covered almost 50% of the total annual production in Europe. The high levels of data provision mean that the datasets presented in Table 3 and in the Annex are highly representative of the practices and subsequent overall environmental performance of the sector.

The report is available for interested parties on the condition that the data in this report may only be used for environmental studies such as Life Cycle Inventory Analysis, Life Cycle Impact Assessment as separate steps or as a whole Life Cycle Assessment.

The database may only be used for environmental studies regarding product development and improvement and the comparison of the entire system of corrugated board packaging with that of other materials. **The database cannot be used for comparisons between the production of primary fibre and recovered fibre-based materials as such.**

LCA methodology, with its systematic, scientific approach, gives an insight into the environmental impact that a product may have **on a case-by-case basis.**

1 In the past, the project was a joint undertaking by three associations FEFCO, GEO (European Association of makers of Corrugated Base Papers) and ECO (European Containerboard Organisation). GEO and ECO merged to become Cepi ContainerBoard, which has since been renamed as Containerboard Europe.

When LCA data is used to make comparative studies, a specific scenario is chosen and the result can and will vary depending on various parameters. It should be clearly understood that, whatever the outcome of a comparative study, the conclusion should not and cannot be generalized.

It is therefore not recommended to use a single message from a comparative LCA study as the basis for lobbying activities.

According to ISO 14044, allocation of the impacts of primary fibre production (the cradle) and waste treatment (the grave) of wood fibre to the phases in between the cradle and the grave of the life cycle should be avoided, wherever possible. In our case this is done by expanding the product system and considering the expanded system with a closed-loop approach.

FEFCO and Containerboard Europe are committed to ongoing and regular updates of the database. The user of the database should therefore check whether it is the latest edition of the database report prior to using the information enclosed. The latest version will always be available online or through direct contact with either of the Associations.

We would like to thank all participants from the industry for providing the necessary input from their plants. Collecting, processing and checking the data is a significant undertaking. The high level of ongoing participation of the membership base of both organisations is highly appreciated.

We are also grateful for the positive response and valuable feedback and comments we have received from users of the previous editions of the database and reports. **We welcome comments on this report and feedback on the experiences of users of the database. Such feedback can only help to further improve the quality and value of future updates!**

April 2026

Eleni Despotou, FEFCO

Paul van Bezouw, Containerboard Europe

DESCRIPTION OF THE PRODUCT SYSTEM

PAPER PRODUCTION PROCESS

Liner and fluting papers can be manufactured from primary wood fibres from sustainably managed forests and/or from recovered fibres from paper for recycling. As a general rule, kraftliner and semi chemical fluting are manufactured from predominantly primary fibres whereas testliner and recycled fluting are predominantly manufactured from recovered fibres.

Production of liner and fluting is typically performed at an integrated pulp and papermill (meaning that the pulp and the paper are produced at one single site, and the wet pulp is pumped directly to the paper machine with no additional drying or transport required).

For mills utilising primary wood fibre, most of the wood is delivered in the form of pulpwood logs. A proportion is also brought in as wood chips, a by-product of nearby sawmills. The pulpwood logs have to be debarked and chipped before pulping. For Kraftliner production, the kraft pulping process is used. This is a highly alkaline cooking process with caustic soda and sodium sulphide as active cooking chemicals. The cooking takes place in a digester at high pressure and a temperature of 150 -170 °C. The pulp yield is normally around 55% (i.e. 1000 kg of dry wood gives 550 kg of pulp).

For semi chemical fluting production, the wood chips are converted into pulp by the semi chemical cooking process. It is a slightly alkaline cooking process most commonly using sodium sulphite and sodium carbonate as active cooking chemicals. The pulp yield is normally around 80%.

The spent cooking liquor is drained off and washed out from the pulp. It contains the wood substance dissolved during the cooking together with the spent cooking chemicals. The spent liquor is concentrated and burnt as a fuel for energy production and recovery of cooking chemicals. The pulp produced is defiberized in refiners, screened and washed before being sent to the paper mill.

For mills utilising recovered fibres, the main recovered paper grade utilised for manufacture of testliner and recycled fluting is old corrugated cases[2], meaning that most of the fibres are recycled in a closed loop system.

The bales of recovered paper are submerged in water and the mixture is agitated so that the paper is broken up to form a pumpable suspension. Large non-paper components such as pieces of plastics, wood, metal and textiles are removed using a "ragger" or "junker" and smaller remaining non-paper components are removed by screening and cleaning. The hot pulp may also undergo a disperging treatment, in which contaminants such as hot melt, wax, ink and coating binders loosen from the fibres and together with small fragments of paper are reduced to fine particles which are no longer visible. Pulp for recycled fibre-based paper for corrugated packaging does not normally undergo a deinking process.

For pulps from both primary fibres and recycled fibres, functional chemicals, fillers and other pulps can be added to give the final paper the properties required.

Figure 1 shows an example of the production stages for a typical paper machine. The wet stock passes through one or two headboxes onto the paper machine. The paper web is formed from the head box onto the wire and dewatered primarily by the action of gravity and vacuum. Further dewatering by mechanical means takes place in the press section where water is taken out of the sheet by pressing between felts. The final drying takes place in the drying section of the paper machine where the sheet runs against steam heated cylinders to get its final dryness of 91-93%. The collected water is reused for diluting the thick stock coming from the stock preparation.

2 Grades 1.04 or 1.05 defined in EN643 European List of Standard Grades of Paper and Board for Recycling, 2013 revision

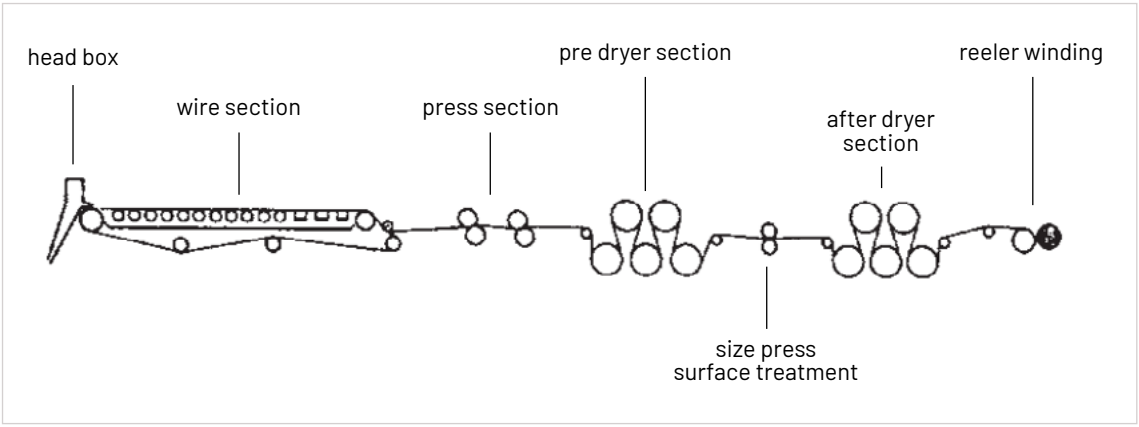


FIGURE 1: EXAMPLE OF PAPER MACHINE FOR CONTAINERBOARD GRADES

Semi chemical fluting is a paper with just one ply and therefore the paper machine has one headbox and one wire. Kraftliner is normally a two-ply product and therefore requires a paper machine with two headboxes and usually two wires. The base brown ply contains the internal machine broke pulp in addition to wood fibres from the usually integrated pulp production and could also contain recycled paper pulp. The top ply is normally wood pulp from the integrated pulp production that is more refined and cleaner to give the top surface the right characteristics and printability. For white surface grades bleached fibres are used for the top ply.

Testliner mostly consists of two plies of paper. Different mixes of recovered pulp stock will be used in each layer. Generally, a better grade of mix is used for the upper layer for reasons of appearance and strength. In order to increase its strength testliner receives a surface treatment in the size press. This involves the application of a starch solution to one or both sides of the sheet. The top ply of testliner is given an even, mostly brown colour by colouring the mass or by means of the size press treatment. This colouring is never given to white top testliners. The addition of special additives (in the mass or by means of the size press) makes it possible to produce testliners with special properties, including extra water-repellent, low-germ and anti-corrosion grades.

Recycled fluting can be a one-ply or two-ply product. Usually, a size press treatment with a starch solution is applied in-line on the paper machine in order to obtain sufficient strength and stiffness properties

After the paper machine there is a slitter winder where the jumbo reel from the paper machine is rewound and cut down to customer reel formats according to customer orders. These reels are weighed, marked, labelled and prepared for shipment to the customer, the corrugated board industry.

Corrugated base papers comprise the largest share of paper and board production in Europe, representing 41.2% of total paper and board production, and 65.4% of packaging paper and board. European production of corrugated base papers in 2024 stood at 33.2 million tonnes. The majority of product is produced from recovered fibres. Approximately 88% of corrugated packaging is derived from recycled content. Corrugated base papers have a paper for recycling utilisation rate of 94.7% and use 66.4% of total paper for recycling volumes used by the industry[3,4].

Table 1 summarises the base paper consumption for corrugated board in 2024.

3 Containerboard Europe statistics
4 CEPI Key Statistics 2024

TABLE 1: BASE PAPER CONSUMPTION FOR CORRUGATED BOARD IN EUROPE 2024
(FROM CONTAINERBOARD EUROPE STATISTICS)

		FIBRE COMPOSITION	
MILLION TONNES	**TOTAL**	**PRIMARY**	**RECYCLED**
KRAFTLINER	4.15	3.17	0.98
TESTLINER	13.86	0.11	13.75
OTHER RECYCLED LINER (SCHRENZ)	1.26		1.26
SEMI CHEMICAL FLUTING	0.52	0.47	0.05
RECYCLED FLUTING	10.86	0.09	10.77
	30.65	**3.84**	**26.81**
		12%	**88%**

NOTE: VALUES SUBJECT TO ROUNDING

CORRUGATED BOARD PRODUCTION

Corrugated board is made from a combination of flat sheets of paper (called "liners") glued to a crenulated corrugated inner medium (called "fluting"). These layers of paper are assembled to one another (typically using a starch glue) in a way which gives the overall structure a better strength.

Most commonly, a single layer of fluting is sandwiched between two liners. This type of construction, as shown in Figure 2, is known as single wall corrugated board.

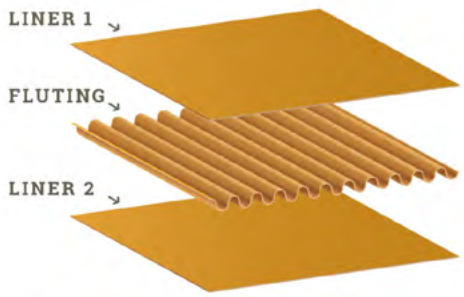


FIGURE 2: SINGLE WALL CORRUGATED BOARD

Double wall and triple wall boards are also available on the market. A corrugated board grade called single face board consists of corrugated medium glued to only one flat liner (See Figure 3 - various definitions after ISO 4046).

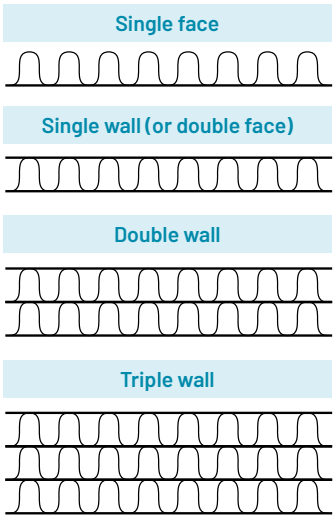


FIGURE 3: CORRUGATED BOARD CONSTRUCTIONS

This ingenious construction forms a series of connected arches, a geometric form that is well known for its ability to support strong weights. This structure gives corrugated board considerable rigidity and resistance. The air circulating in the flutes also serves as an insulator. These properties of strength and insulation mean that, when converted into boxes, corrugated board provides excellent protection of the packed goods against damage and temperature variations.

The corrugated board industry is made up of three types of plant:

- **Sheet plants** – these take in liner and fluting paper and produce corrugated board in sheets which is sold on to box plants for production of boxes
- **Box plants** – these take in sheets of corrugated board and convert them into corrugated boxes
- **Integrated plants** – these take in liner and fluting paper and produce corrugated board, which they then convert into corrugated boxes. They may also purchase some corrugated board in sheets from other sheet plants to supplement their own production. Conversely, they may also sell some corrugated board in sheets to other box plants.

The majority of production in Europe is in integrated plants.

Reels of fluting and liner are fed into a machine called a corrugator (Figure 4). The fluting paper is conditioned with heat and steam and fed between large corrugating rolls that give the paper its fluted shape. Starch is applied to the tips of the flutes on one side and the inner liner is glued to the fluting. The corrugated fluting medium with one liner attached to it is called single face web and this travels along the machine towards the double backer, where the single face web meets the outer liner and forms corrugated board. A number of layers of single faced web may be built up to produce double and triple wall corrugated board (Figure 2). The corrugated board is slit into the required widths and cut into sheets which are then stacked or palletised.

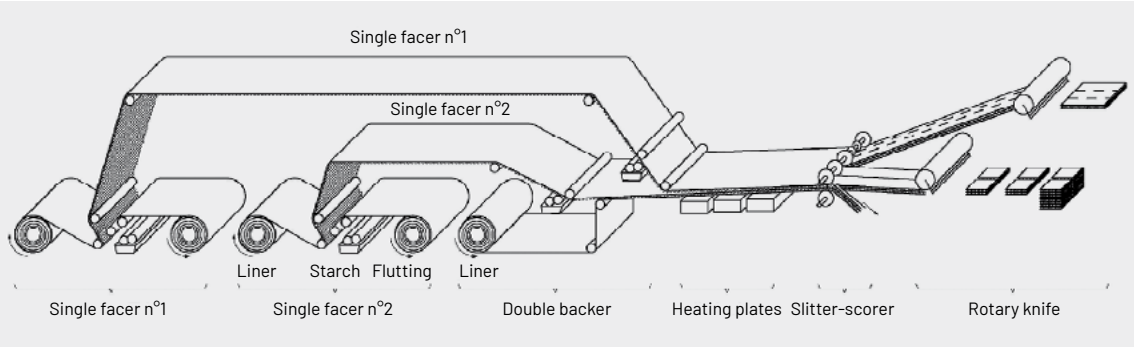


FIGURE 4: CORRUGATED BOARD PRODUCTION

The main conversion steps when converting corrugated sheets into corrugated boxes include printing, slotting, folding and gluing. The printing and gluing steps may be absent, depending on the specific design of the corrugated box. Depending on design, corrugated boxes are typically delivered to the end user as flat blanks (Figure 6) ready for erection (Figure 7). This ensures space efficiency during distribution.

Most boxes are printed in one or more colours to identify the product they are going to contain, the product manufacturer, the box manufacturer and other information regarding the distributed goods. Different converting operations are carried out according to the customer's specification and according to the type of packaging. The two main categories are the regular slotted box and the die-cut box. The latter concerns packaging that requires a very precise cutting and which can have a complex design.

Regular slotted boxes are usually produced with an in-line flexographic Printer/Slotter/ Folder/Gluer which, in one operation, prints, cuts, folds and glues the board into its final shape. The die-cut boxes are manufactured on a die-cutter (rotary or flatbed) which cuts and creases the board. After converting, the corrugated packaging is put on a pallet and delivered to the customer.

CORRUGATED BASE PAPERS AND CORRUGATED BOARD

This study covers the production of the following grades of corrugated base papers[5]:

- Kraftliner, including brown kraftliner, white top kraftliner and white coated kraftliner
- Testliner, including brown testliner, brown kraft top liner, uncoated white top testliner, coated white top testliner, and mottled testliner
- Semi chemical fluting
- Recycled fluting, light-weight recycled medium and recycled dual papers.

These materials are used to manufacture corrugated board, which is then converted into corrugated packaging solutions (corrugated boxes) and other corrugated board products such as point of display stands. This study also covers the conversion of corrugated base papers into corrugated board and corrugated boxes.

The base weight of corrugated base papers can vary significantly but for liner it is typically in the range of 90-200gsm and for fluting it is typically in the range of 90-150gsm. The average base weight of corrugated base papers produced in the mills participating in this data survey was 130gsm.

The base weight of corrugated board depends on the specific corrugated base papers being used in the construction, plus the kind of flute (wave type) used. Different wave types lead to different heights of the corrugated layer and to different paper consumption (due to the take-up factor). In Table 2 indicative figures are given for different flute types, as an example.

5 As identified in European List of Corrugated Base Papers, Cepi Containerboard, 5th Edition, September 2015 (available at https://containerboardeurope.org/wp-content/uploads/2025/06/European-List-of-Corrugated-Base-Papers-English.pdf)


TABLE 2 : FLUTE TYPES

Flute	Flute height* mm	Number of flutes per m length of the corrugated board	Take-up factor	Glue consumption g/m² glue layer
A	4.8	110	1.50-1.55	4.5-5.0
B	2.4	150	1.30-1.35	5.5-6.0
C	3.6	130	1.40-1.45	5.0-5.5
E	1.2	290	1.20-1.35	6.0-6.5
F,G,N	0.5-0.8	400-550	1.15-1.25	9.0-11.0

*FACINGS EXCLUDED

The take-up factor governs the amount of fluting material required to manufacture the corrugated board. It allows for the fact that, when laid out flat before converting, the area of fluting material required to manufacture a defined area of corrugated board is greater than the surface of the converted board itself. For example, a typical take-up factor for C-flute is 1.43, meaning that 1.43m² of fluting (measured flat) is required to manufacture 1m² of converted corrugated board, as shown in the example in Figure 5.

FIGURE 5: ILLUSTRATING THE TAKE-UP FACTOR

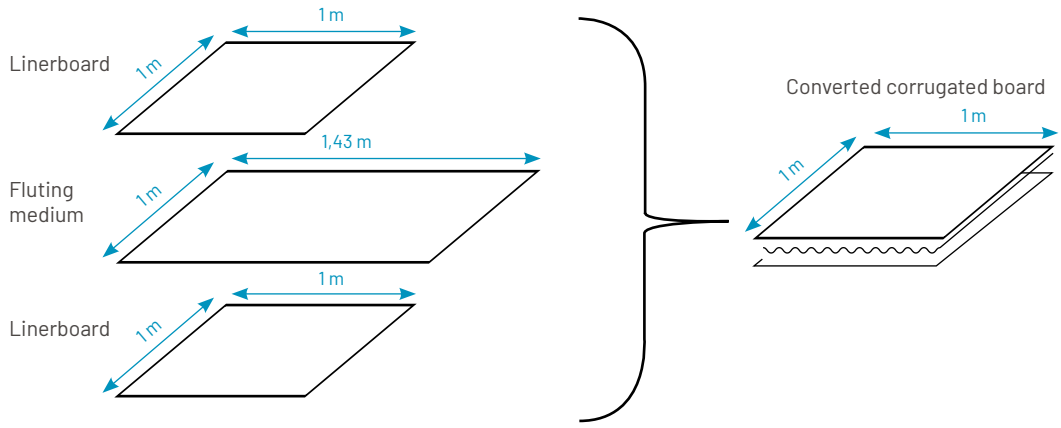

- Example: FEFCO Code 0201
- Box weight: 650 g
- Dimensions : 575 x 385 x 225 mm (L x B x H)
  corrugated board C flute
- Facings: Kraftliner 175 g/m², Testliner 175 g/m²
- Corrugating
- Medium: Recycled Fluting 140 g/m²

The composition of the corrugated board is then:

	g/m²
Kraftliner	175
Recycled Fluting	1.43 x 140 = 200
Testliner	175
Glue	2 x 5 = 10
Grammage	**560**

The base weight of corrugated board can vary significantly, from less than 300gsm to more than 900gsm. The average grammage of corrugated board produced by manufacturers participating in this study was 469gsm. The average grammage across the entire industry is 497gsm[6].

The corrugated board manufacturer can give the weight of the sheet before die-cutting. For a standard type construction the weight can also be calculated using the International Fibre Board Case Code published by FEFCO. In this code the form of the box blank is shown and by using the box dimensions it is possible to calculate the total length and width of the blank. Adding a 20 mm broad strip to the edges of the blank gives a fair estimate of the sheet area before die-cutting.

FIGURE 6: BOX BLANK EXAMPLE


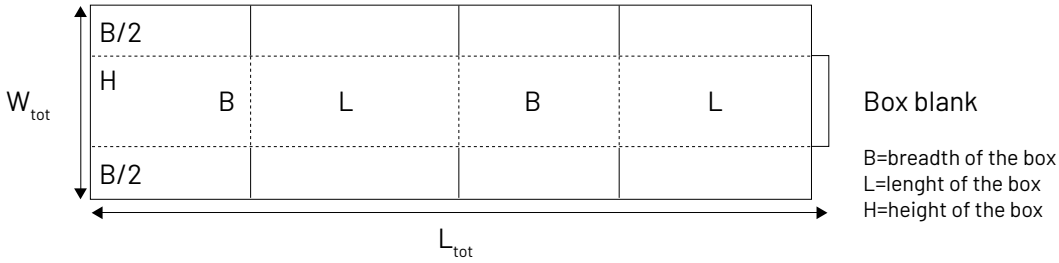


FIGURE 7: CONVERTED BOX

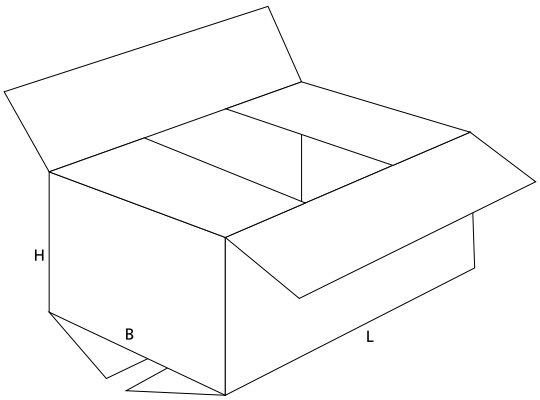

Considering an example from Figure 6 where L tot = 1.95m and W tot = 0.61m, the dimensions of the sheet are:

$A_{sheet} = (1,95 + 0,04) \times (0,61 + 0,04) = 1,2935\ m^2$
and the weight:
msheet = 1,2935 x 560 = 724 g

Assuming 3% as corrugator trimmings (i.e. $\eta_{corrugator}$ = 0.97, a common value for modern corrugators), the consumption of liner and fluting can be calculated as follows:

		g/box
Kraftliner	175 * 1.2935/0.97 =	233
Recycled Fluting	200 * 1.2935/0.97 =	267
Testliner	175 * 1.2935/0.97 =	233
Glue	10 * 1.2935/0.97 =	13
		746

Total (shavings) = 746 - 650 = 96 g/box = 12.9% of the input.

Please note that this is only an example of a particular box of a certain construction. Corrugated board boxes are far from standardised. They show a huge variation in composition, design and appearance. Boxes are usually tailor made to fit the user's needs and requirements which are determined by the product to be packed. The percentage of trimmings/shavings vary according to the design of the packaging. Since standard boxes do not exist, the database is set up in a flexible way giving the user the possibility to make calculations for any composition needed and using project specific assumptions on transport distance, waste management scenarios etc.

METHODOLOGY QUESTIONS

BOUNDARIES AND DECLARED UNIT

The gate-to-gate life cycle inventories for each grade of corrugated base papers are presented in the Annex according to the following declared unit:

> ***one air dry tonne (1000 kg) of net saleable paper at the parent reel, before conversion to finished products***

The gate-to-gate inventory for conversion of corrugated base papers into corrugated board and boxes is presented in the Annex according to the following declared unit:

> ***one tonne (1000 kg) of printed, slotted, folded and glued corrugated boxes***

The compiled results presented in Table 4 of this report relate to the production **one tonne (1000kg) of printed, slotted, folded and glued corrugated boxes.** The system boundaries considered for these results consider and quantify the flows to and from the technosphere and the environment from the papermill in-gate to corrugated box plant out-gate, as illustrated in Figure 8. In order to complete a cradle-to-gate analysis for corrugated boxes, life cycle data for the items shown in red must be added.


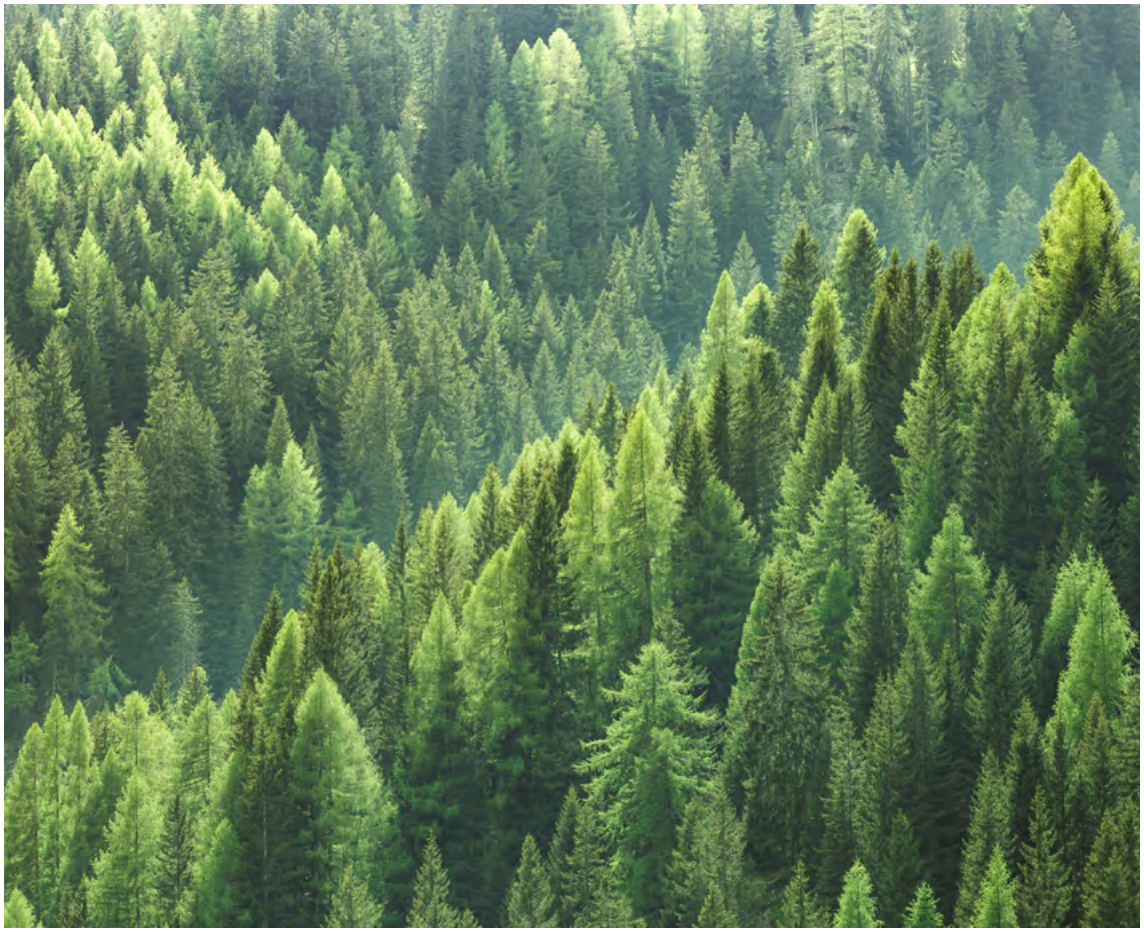


FIGURE 8: SYSTEM BOUNDARIES FOR THE RESULTS SHOWN IN TABLE 3

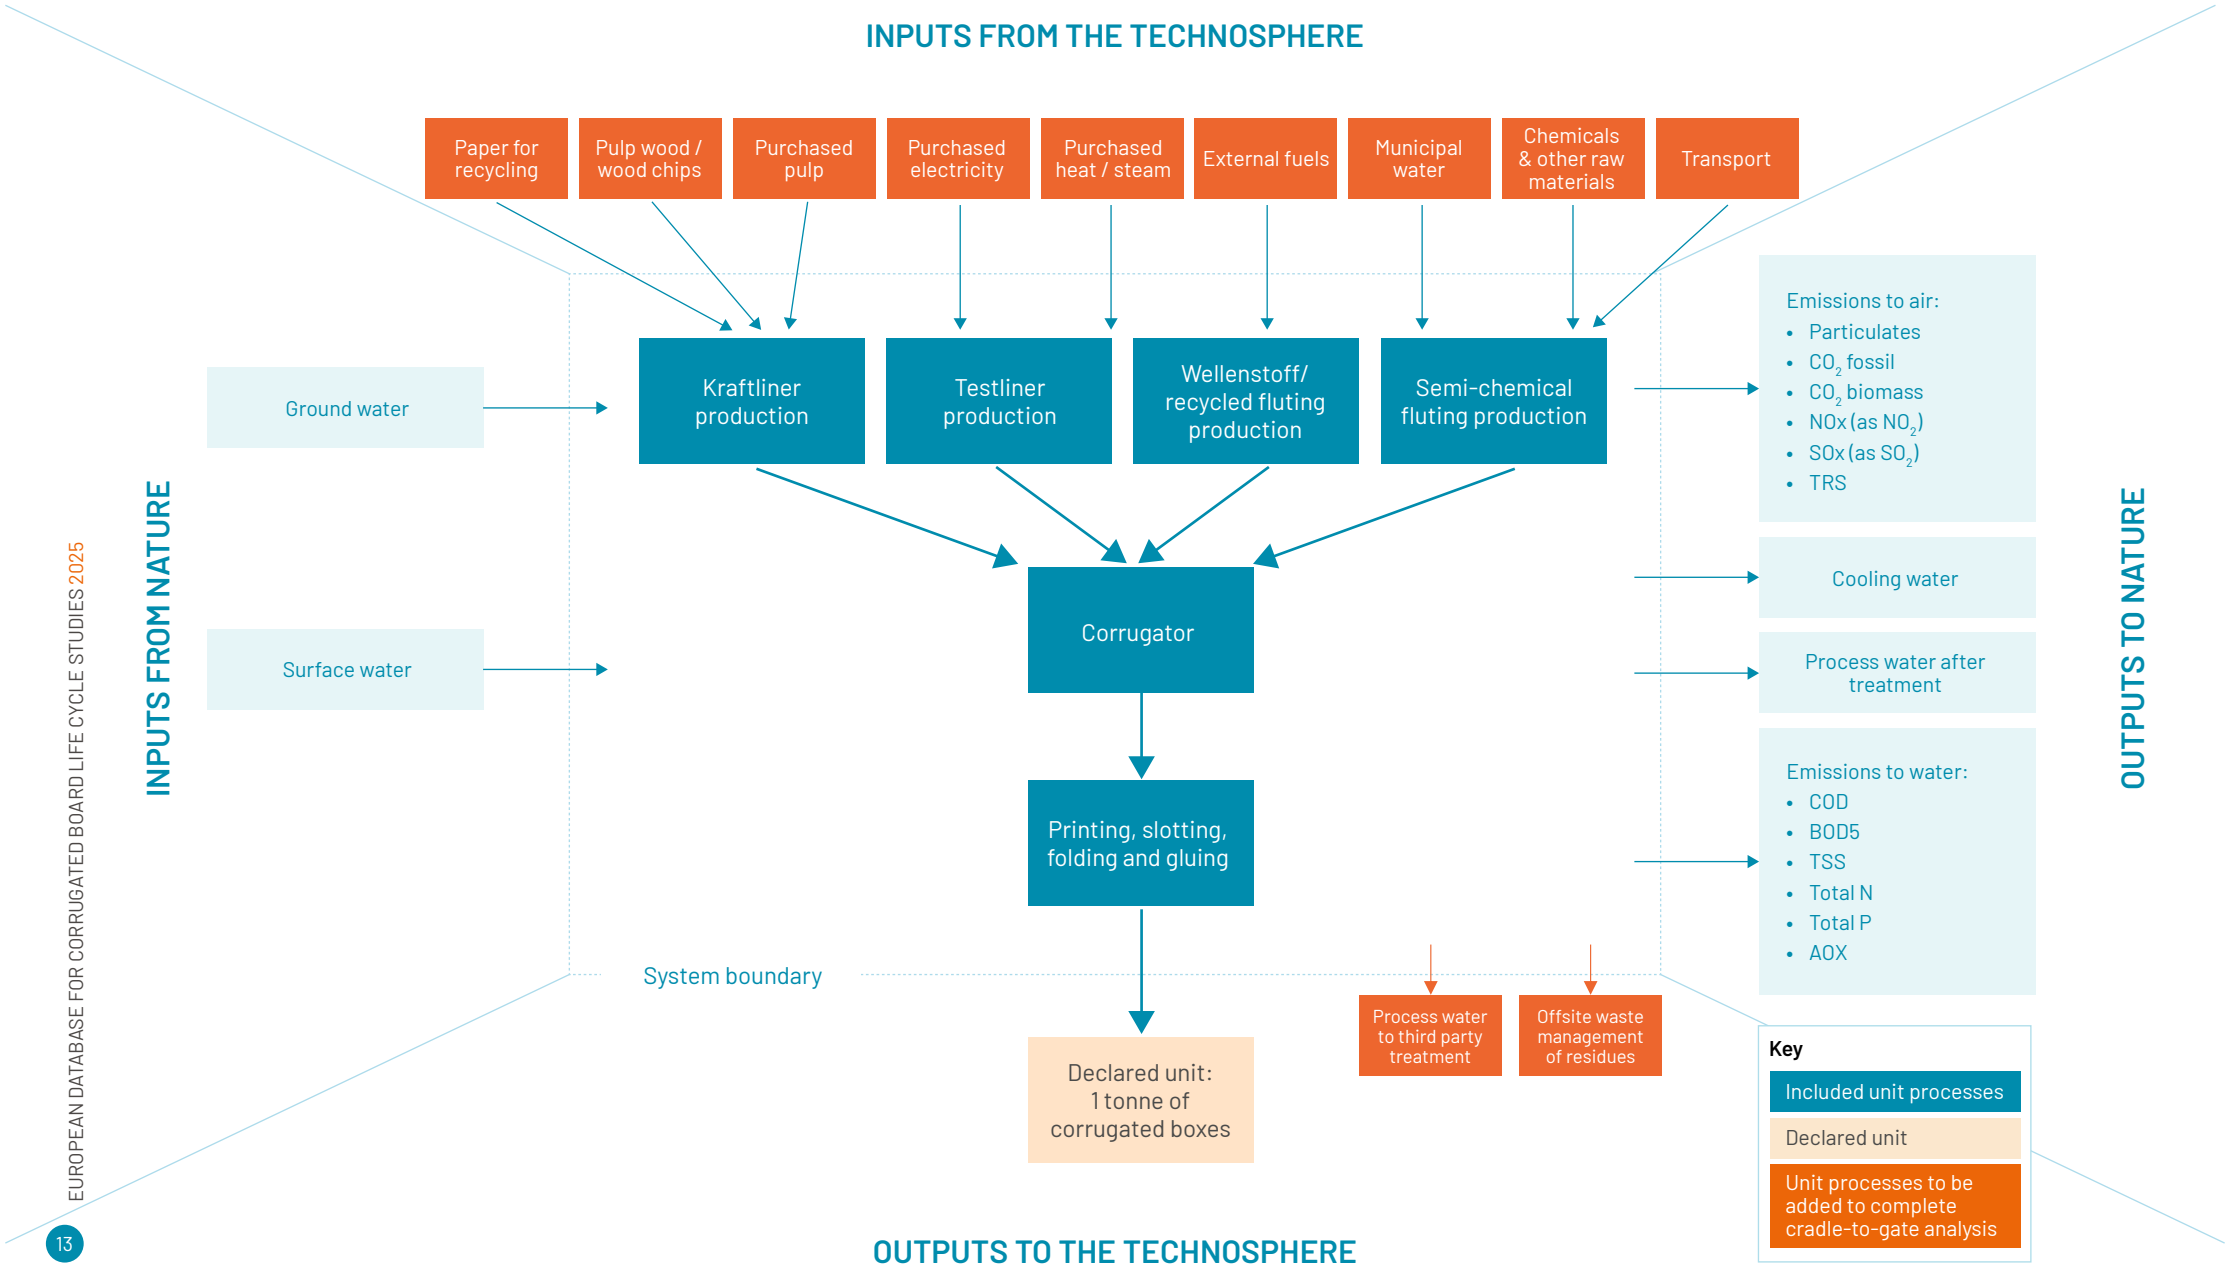

In addition to the compiled results shown in Table 4, separate data is presented in the Annex for production of the corrugated base paper grades (kraftliner, testliner recycled fluting and semi chemical fluting) and for the conversion of corrugated base papers into corrugated boxes (corrugating plus printing, slotting, folding and gluing). The system boundaries for these separate datasets are described below.

SYSTEM BOUNDARIES FOR CORRUGATED BASE PAPERS

The system boundaries of the life cycle inventories for corrugated base papers presented in the Annex include all activities within the pulp and papermill boundaries. Thus, included in the inventory are all the inputs and outputs (from/to the technosphere and from/to nature) associated with:

- Pulp production from pulp wood/wood chips
- Pulp production from paper for recycling
- Stock preparation, refining, and operation of the paper machine
- Drying
- Reeling and reel winding
- Supporting activities used in paper production, e.g. water and solid waste treatment, onsite electricity and heat/steam generation.

Figure 9 summarises the system boundaries. These system boundaries are representative of the core processes.

In cases where the mill produces and sells excess energy (e.g. electricity or steam), this is treated as a multifunctional situation. The system provides two functions (i.e. corrugated base paper plus energy). In this case, subdivision has been applied – i.e. only the inputs and outputs that are allocated to the paper production are reported in the life cycle inventory.

No allocation was made to by-products such as tall oil, turpentine and wood/bark chips, so the reported inputs and outputs include the production of these by-products.


For those paper mills producing more than one grade of paper and/or market pulp it is necessary to allocate inputs and outputs to the different paper grades or pulp. Mill staff who filled in the questionnaire have made the allocation according to causality.

Data has been collected relating to the following key non-fibre inputs to the pulp and papermaking processes:

- Sulphuric acid (H_2SO_4)
- Sodium hydroxide (NaOH)
- Oxygen (O_2)
- Hydrogen peroxide (H_2O_2)
- Sodium Chlorate ($NaClO_3$)
- Calcium oxide (CaO)
- Chlorine dioxide (ClO_2)
- Sodium bisulphite ($NaHSO_3$)
- Ground calcium carbonate (GCC)
- Precipitated calcium carbonate (PCC) – purchased
- Clay
- Wet strength agent
- Dry strength agent
- Synthetic binders (latex)
- Starch – maize
- Starch – potato
- Starch – corn/wheat
- Starch - cationic

The total mass of other non-fibre inputs not listed above is below 1% of the paper weight. As a general rule, these other non-fibre inputs could have been omitted from the study as insignificant. However, for completeness all non-fibre inputs for which data was reported by more than 6 mills have been included in the inventory.

FIGURE 9: GATE-TO-GATE SYSTEM BOUNDARIES – PRODUCTION OF CORRUGATED BASE PAPER

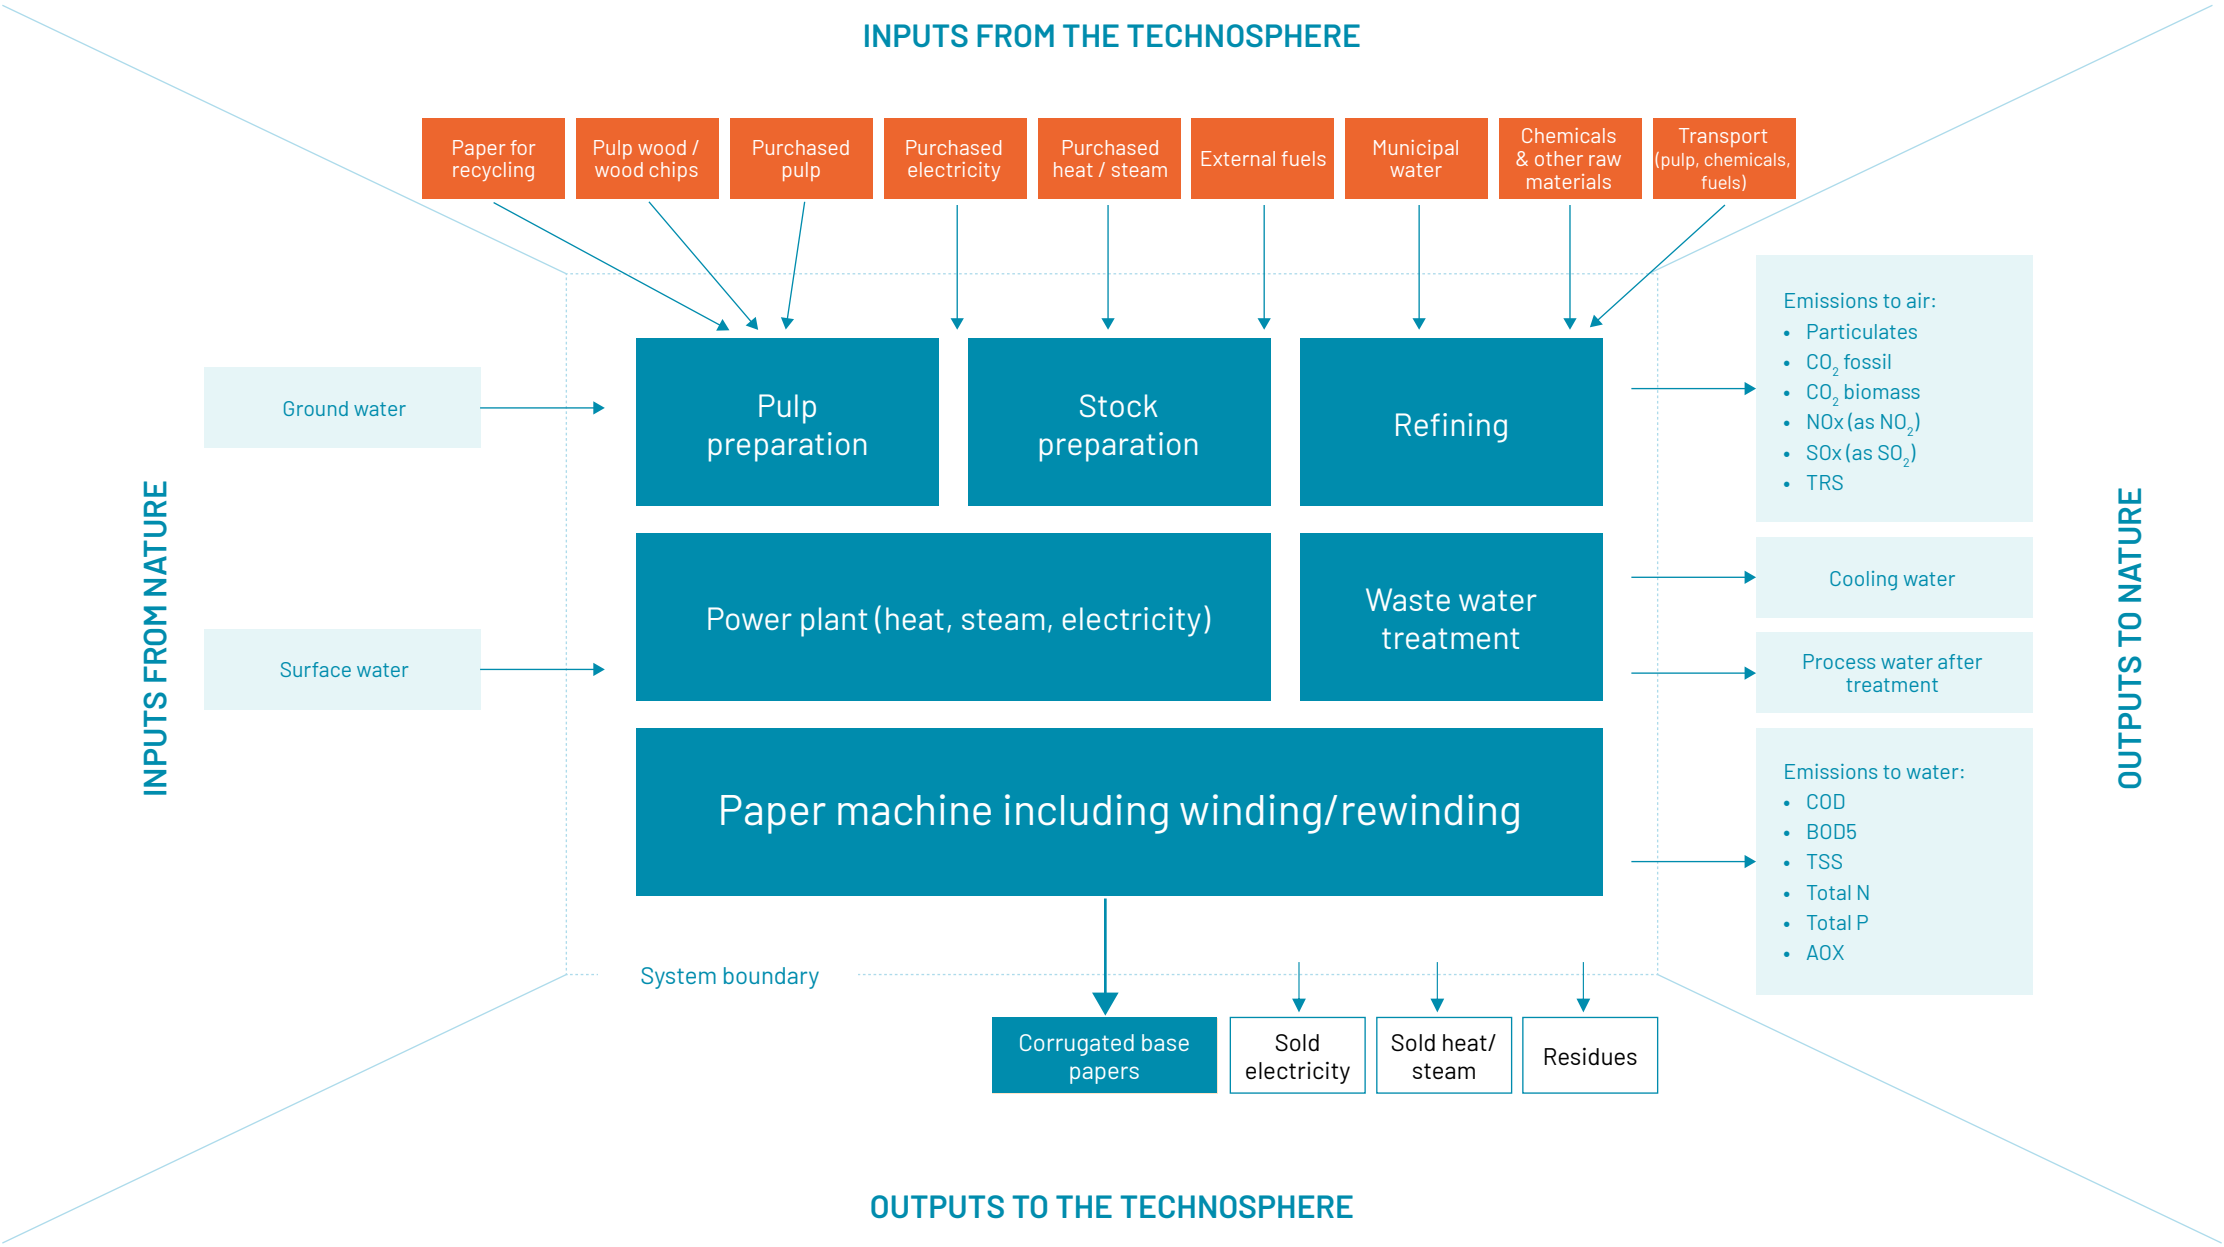

SYSTEM BOUNDARIES FOR CORRUGATED BOARD AND BOXES


The system boundaries of the life cycle inventory for conversion of corrugated base papers into corrugated board and boxes presented in the Annex include all activities associated with assembling corrugated base papers into corrugated board and converting corrugated board into corrugated boxes. Thus, included in the inventory are all the inputs and outputs (from/to the technosphere and from/to nature) associated with:

- The corrugator machine
- Printing
- Slotting
- Folding
- Gluing
- Supporting activities used in conversion process, e.g. onsite heat/steam generation, onsite wastewater treatment.

Figure 10 summarises the system boundaries.



FIGURE 10: GATE-TO-GATE SYSTEM BOUNDARIES – PRODUCTION OF CORRUGATED BOARD AND CORRUGATED BOXES

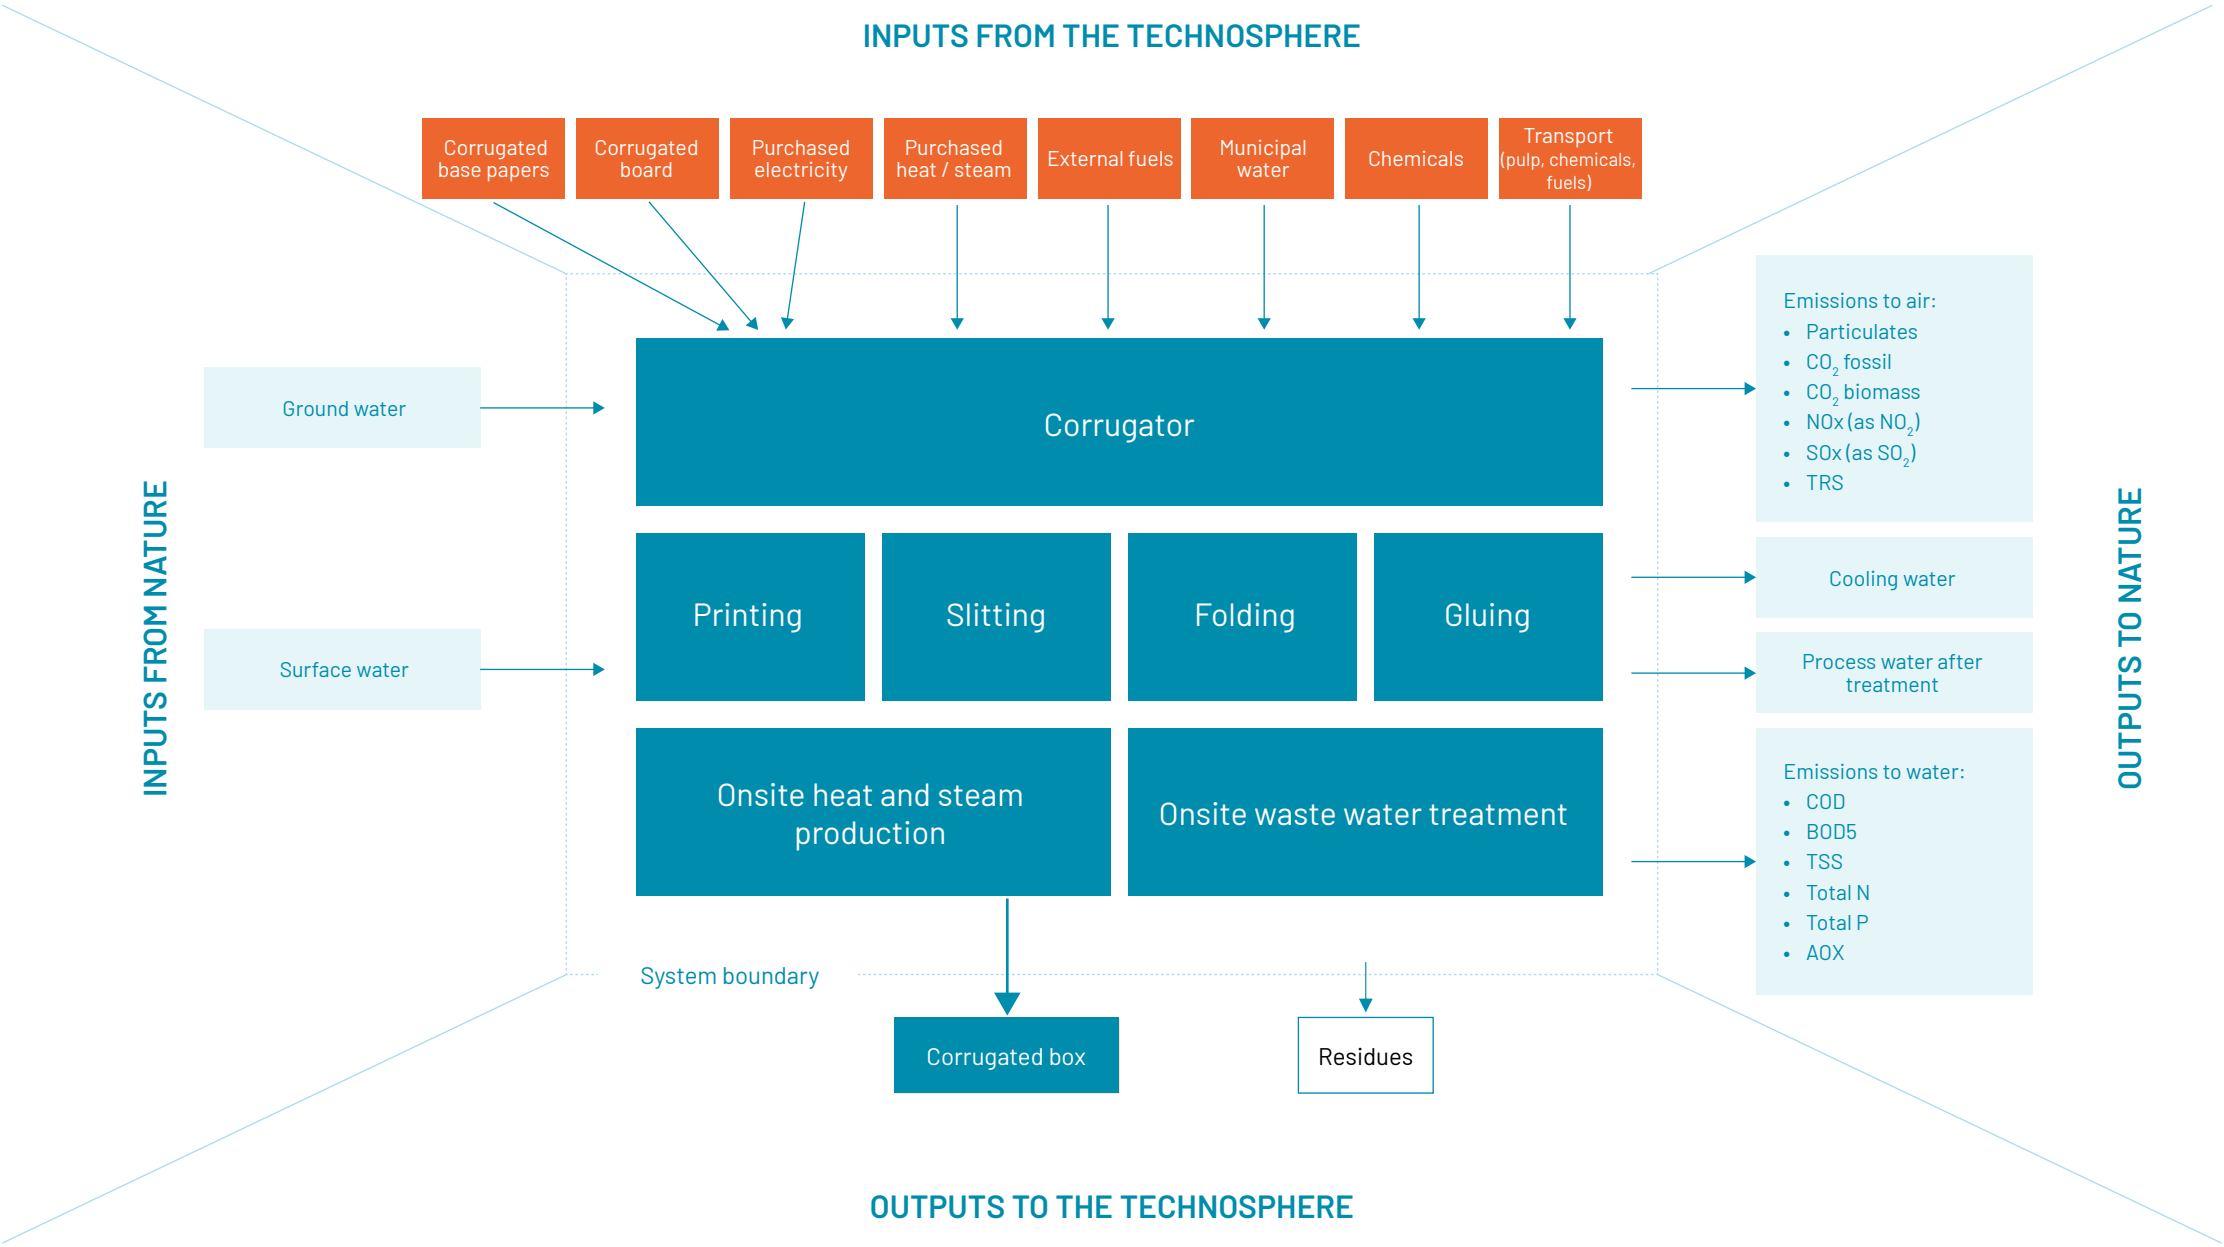

THE CLOSED-LOOP APPROACH

Many of the corrugated base paper grades considered in this life cycle database incorporate recovered fibres, and all of the paper grades achieve a high level of recycling after use, and the fibres themselves will be recycled multiple times.

This potentially introduces complexity to the analysis, as choices have to be made regarding the allocation of impacts between the primary fibre-based paper and the recovered fibre based paper, in particular:

- the impacts of the primary fibre pulp production and the final waste treatments
- the avoided impacts resulting from the recycling.

However, for the production of corrugated base papers a closed loop recycling situation is considered – i.e., the recovered material is assumed to be used in the same product life cycle. In this case, the collected fibres displace the input of primary fibres, and the need for allocation is avoided (as per ISO 14044).

Thus, to simplify the system, recycling of corrugated board may be considered as processing of the primary fibre after use in corrugated board or as raw material processing for the secondary product (or recycled products), also used in corrugated board. This is an appropriate and justifiable simplification as the main raw material for the recovered paper mills producing corrugated base papers is used corrugated board, thus flows in and out of the system of other kinds of paper are ignored.


The closed-loop approach requires that the total system is considered during a certain period of time and a specific geographic area. A simplified system for a closed-loop corrugated board packaging system is given in Figure 11.

There are different definitions for recycling and recovery (which could mean collection of waste or treatment of waste), depending on the application. This of course leads to the publication of different recycling/recovery rates.

For example, CEN 13440:2003 describes a procedure for calculating the rate of material recycling to demonstrate compliance with the recycling targets given in the Packaging and Packaging Waste Directive 94/62/EC (as amended by 2018/852/EC).

For the system described in Figure 11, fibres are recovered (in the sense of collected) from shavings from the production of corrugated board and from collected corrugated board after use, and following that are recycled in a papermaking process to become new paper.

FIGURE 11: ILLUSTRATING THE CLOSED-LOOP APPROACH

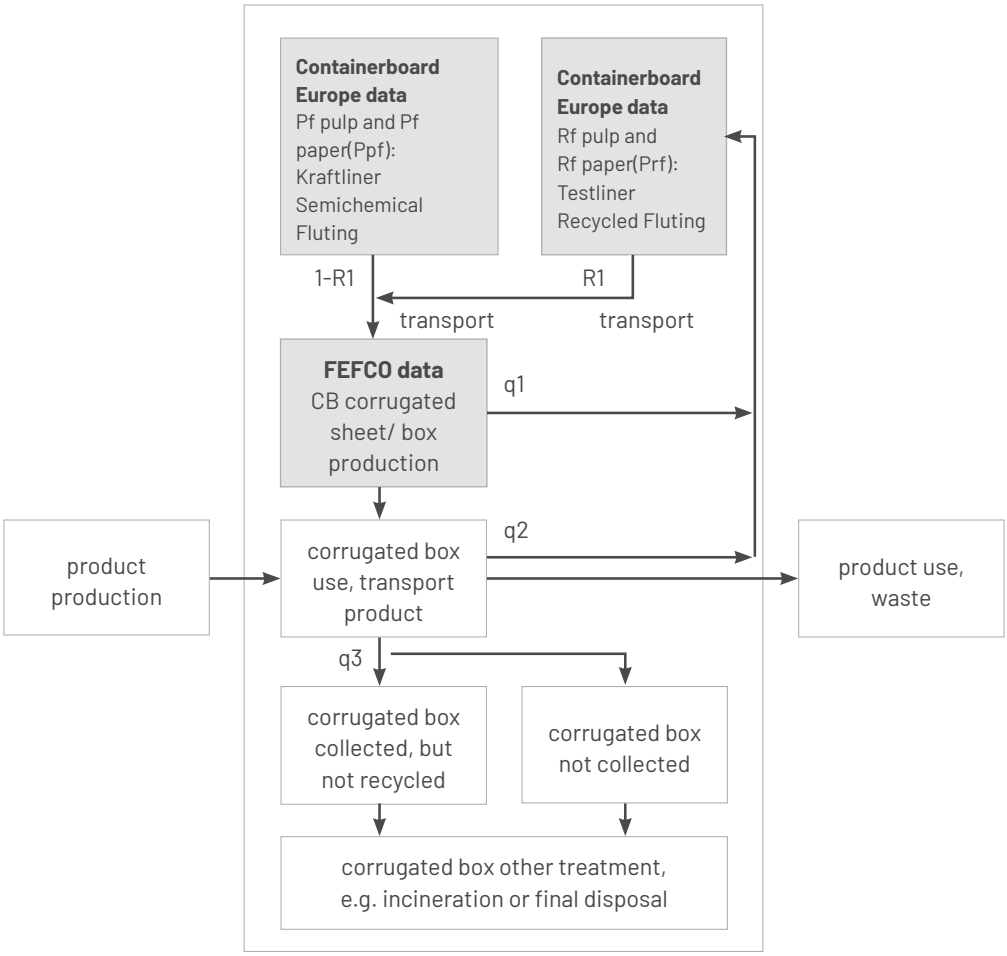

The recycled fibre content (R1) for this report is defined as total recovered fibre recycled from shavings (q1) as well as from used corrugated boxes (q2) divided by the total paper production used for corrugated board production.

q1 is defined as the weight of production shavings from corrugated board production divided by the weight of the base paper used for the corrugated board production. These production shavings are always recycled. The amount depends on the reference unit. For Europe, the typical amount is about 100 kg/tonne corrugated product, for the converted box it is 120 kg total shavings/tonne.

q2 is defined as the weight of collected corrugated board after use, effectively recycled divided by the weight of the base paper used for corrugated board production. Recycling is the common practice for collected (and if necessary sorted) corrugated board, but it may be that fibres are lost from the loop because not all corrugated packaging is collected. For corrugated board that is not recycled, other recovery options, such as incineration with energy recovery may take place. According to an estimation based on CEPI statistics for 2014, about 87% (R2) of the corrugated board used in Europe was collected and recycled.

In a simplified system for closed-loop corrugated board packaging, this means that the percentage of recovered material is equal to $(R2 \times [1 - r_{sh}]) = 87\% \times [1 - 0.120] = 76.6\%$ of the input of the base papers would be recycled after use if all the recovered corrugated board was recycled only within the system. This is a simplification as a small part of the recovered fibre input originates from, for example, graphic paper loops and some collected corrugated board is recycled into other paper grades[7].

7 Based in the equation presented in Figure 11, the life cycle of the paper fibres in corrugated packaging is estimated to be fully circular at 87%. Within the context of the European recovered paper production environment, recovered fibres will typically be sent for use at the nearest appropriate recycled paper manufacturer. This may not necessarily be a packaging paper line. Some 60% of packaging is recovered at mills producing recycled paper for packaging, some 12% originate from other paper types such as recovered newsprint and the rest, 12% is clippings and trimmings from corrugating and conversion manufacturing.

For the purposes of this document, imports and exports of the corrugated board system are ignored, as are used packaging imports and exports. The application of this specific assumption means that the recycling rate of corrugated board (shavings + used packaging) is equal to the recovery rate of these products.

Table 2 shows that the average R1 for Europe in 2024 is about 88%. In this simplified approach this roughly corresponds with the total amount of collected shavings and used packaging as a percentage of the weight of the input of the base papers for the corrugated board production ([q1 + q2]/total paper production =~ 90%), showing the validity of the closed-loop approach.

Note r_{sh} is not included in the calculation of the recycling rate according to the Directive on Packaging and Packaging Waste 94/62/EC and R2 does not include organic recycling as defined for the same purpose. Therefore, the recycling rate differs from the rate calculated to assess compliance with the recycling targets according to the Directive.

DEFINITIONS AND CALCULATIONS OF RECOVERY AND RECYCLING

Definitions of recovery and recycling EN 13193

Definitions set for the Directive on packaging and packaging waste 94/96/EC, as amended by Directive 2018/852/EC.

Recycling: any recovery operation by which waste materials are reprocessed into products, materials or substances whether for the original or other purposes. It includes the reprocessing of organic material but does not include energy recovery and the reprocessing into materials that are to be used as fuels or for backfilling operations.

Material recovery: any recovery operation, other than energy recovery and the reprocessing into materials that are to be used as fuels or other means to generate energy. It includes, inter alia, preparing for re-use, recycling and backfilling.

Packaging waste: any packaging or packaging material covered by the definition of waste laid down in Article 3 of Directive 2008/98/EC, excluding production residues.

Calculation of recycling rate EN 13440: 2003

$r_\eta = (\delta 1 + \delta 2)/(\alpha + ß - \gamma)$

r_η = recycling rate of used packaging

$\delta 1$ = material for organic recycling

$\delta 2$ = material for material recycling

α = quantity of packaging put on the market for one way use

ß = quantity of reusable packaging put on the market and used for the first time

γ = that part of used packaging which is not available for recycling due to other secondary uses

CEPI Recycling rate calculation

Recycling rate = utilisation of paper for recycling + net trade of paper for recycling, compared to paper & board consumption.

In 2017, the European Paper recycling rate (for all grades and products) was 72.3% (CEPI key statistics 2017) in Europe (EU-27 countries + Norway and Switzerland), meaning that over 55 million tons of paper-based products have been collected for recycling.

Concerning the Paper & Board Packaging recycling rate in Europe, according to CEPI statistics 2017, it amounts to 82.1%.

DATA DESCRIPTION

QUESTIONNAIRE / DATA COLLECTION FOR CORRUGATED BASE PAPERS

The data was collected via a bespoke questionnaire issued to the mills requesting information on the flows into and out of the integrated pulp and paper mill. The questionnaire was designed to cover the main inputs to and outputs from the pulp and papermaking processes, including the supporting ancillary processes such as energy production, wastewater treatment, etc. The questionnaires were reviewed by technical experts and the peer reviewer before issuing to the industry. The questionnaires were issued during 2025, and data was provided representative of production scenarios in 2024.

The data for semi chemical fluting and kraftliner represent approximately 86% of the total annual production of corrugated base papers from primary fibres in Europe. These paper grades are produced in large mills, located in Austria, Finland, France, Portugal, Poland, Slovakia and Sweden. Their total production was 5,063,000 tonnes net saleable paper in 2024. The mills each have an annual production of semi chemical fluting or kraftliner of between 87,000 and 810,000 tonnes net saleable paper. The data for the production of testliner (including white top testliner) and recycled fluting were collected from mills, together producing about 63% (16,303,000 tonnes) of the total annual production of corrugated base papers from recovered paper in Europe (EU-27 countries plus Norway, Switzerland and UK). They were provided by paper mills in Austria, Belgium, Croatia, Czech Republic, France, Germany, Hungary, Italy, the Netherlands, Poland, Romania, Serbia, Spain, Sweden and the United Kingdom. The mills each have an annual production of testliner and/or recycled fluting of between 29,000 and 1,152,000 tonnes net saleable paper. The data for the production of white top testliner are included in the average of testliner.

For all papers, data was collected covering the average market and technology situation for the calendar year 2024. The collected data was sense-checked by technical experts and compiled as a weighted average representing production of each paper grade in 2024.

DATA COLLECTION FOR CORRUGATED BOARD AND BOX PRODUCTION

In order to gather data relating to converting, a questionnaire was designed covering the main inputs to and outputs from corrugated board production and corrugated box production processes. The questionnaires were reviewed by technical experts and the peer reviewer before issuing to the industry.

The data on corrugated board production and production of corrugated boxes are based on 397 plants. These were mostly integrated plants with corrugated board and box production on the same site. 271 integrated plants participated in the survey, out of a total of 537 plants across Europe[8]. The plants were located in Austria, Belgium, Bulgaria, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Ireland, Italy, Latvia, Lithuania, the Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom. Together they produced 11,340,000 tonnes of corrugated board, which is approximately 46% of the total annual production of corrugated board products in Europe. The production sites have an average annual production of corrugated sheets and boxes of 36,378 tonnes, varying from <800 – 172,000 tonnes each.

WEIGHTED AVERAGES

The Annex presents the weighted averages of the inputs into and outputs from the sites (i.e., gate to gate) per tonne net saleable product for each paper grade and for corrugated board/boxes for 2024 from the participating paper mills and corrugated board and box making plants. It is important to understand that the figures do not represent a certain mill or plant with a certain technology. On the contrary the figures represent

8 FEFCO Annual Statistics 2024

a “virtual mill” and a “virtual converting plant” utilising different technologies. The technology which is applied in the participating paper mills and corrugated board plants is not the same.

For example: some mills use a combined heat power generation, some wastewater treatment is external, a large variety of additives is used. In some cases, this leads to a large variation of inputs and outputs between the mills. Furthermore, different inputs and outputs are strongly interrelated, so a mill can be high in one input compared to the others but low in another input, but a mill cannot be low or high for both. Therefore, no range of the data is given to prevent studies from being made using a false combination of highest and lowest data.

Due to confidentiality requirements by the mills, it is not possible to split input and output data per country. Similarly, a split in applied technologies is not possible.

In Table 4, the separate life cycle inventories for corrugated base papers and for corrugated board and box production are combined to compile the life cycle inventory for an average tonne of corrugated boxes, considering both the production of the corrugated base paper and the conversion of the corrugated base papers into corrugated board and conversion of the corrugated board into boxes. For this average corrugated box scenario, the following composition has been assumed:

- Kraftliner 13.5%
- Testliner and other recycled liner 45.2%
- Semi chemical fluting 1.7%
- Recycled fluting 39.5%

These relative shares are calculated from the relative consumption that is found in Table 1. The relative shares are used to calculate the inputs and outputs for the weighted average corrugated base paper. The paper production inputs and outputs are then multiplied with the average input of paper (1.12 tonne/tonne corrugated board product) and added up to the inputs and outputs per tonne of corrugated board product as reported in the Annex. This total includes the production of the paper that is used to produce the corrugated board, including the 12.0% losses that are reported as “paper for recycling”. It has to be kept in mind that the industry averages for inputs of paper, glue and starch are used. As previously highlighted, corrugated board boxes are far from standardised and inputs of paper, glue and starch depend on the box design.

MATERIAL INPUTS

Raw Material

The wood input has been reported as bone dry solid wood under bark. The species are specified, although in the datasets they are reported only as softwood or hardwood. 92% of the pulp wood used for the production of corrugated base papers by the companies returning the survey was certified and third party verified as being sourced from sustainable managed forests and delivered through a certified chain-of-custody system (PEFC or similar). A pulp yield (oven dry pulp/oven dry wood) of 54-56% is normal for Kraftliner. A high pulp yield of 80-85% is normal for Semi Chemical Fluting. The input of recovered paper has been reported as total weight including moisture and other materials (sand, metal objects, plastics, wood etc.). In European countries the water content of recovered paper is generally assumed to be about 10%. The total input of recovered paper is given. The content of other materials in the recovered paper is about 5%. These materials are eliminated from the pulp as rejects during the pulping. It is estimated that about a third of these rejects are materials that were associated with the previous use of the paper (for example, staples, paper clips, tags, adhesive labels, unrecovered fibres, etc). The remaining two thirds is material that is not in any way associated with the previous use of the paper (for example, foreign items such as textiles, plastic packaging, glass, sand and grit, etc). The main raw material inputs for corrugated board production are different grades of paper. The liners are used for the surface layers of the corrugated board, fluting is used for the corrugated layers. There are endless possibilities for the composition of corrugated board. The amount of the different grades of paper and glue used as input for the corrugated board production varies accordingly. These inputs should be considered when the LCA of a certain box is studied. An example is given in Figure 6. This should be kept in mind when considering the averages for paper consumption and the additives for corrugated board production in Table 4.

Chemicals and other non-fibre inputs

Data were collected for chemicals and other non-fibre inputs which may be used either within the process or as additives. Chemicals are given as dry weight. Some of the inputs have been reported grouped together according to their function in the mill. The functional additives, mainly starch, influence the properties of the paper, whilst process additives are used to guarantee that the process of paper production runs smoothly or to increase the production. Water treatment additives include additives used for all water treatment on the site, including the treatment of water for the power station, paper production and waste water treatment if this is done internally. The different mills use a large variety of process and water treatment chemicals. Those that are commonly used and are above the cut-off criterion per mill are reported in the database. A very limited quantity of other additives, e.g. synthetic polymers (polyethylenamine, polyacrylamide, polyvinylamine) are being used. The main input for corrugated packaging is starch glue, containing starch and small amounts (less than 0.5 kg/tonne nsp) of caustic soda, borax, and wet strength agent. Only a few plants laminate the board and/or add a protective coating. All reporting plants that print the board use the flexo printing technique. For box making cold glue and small amounts (< 0.1 kg/tonne nsp) of hot melt, tape (paper or plastic), plastic tear strip and stitch wire are used.

Packaging

Data on cores and other packaging materials associated with paper reels and for packaging materials used around corrugated products was not collected and updated for 2024. Looking at previous data collections, the values showed little change over the years and other LCA studies show that the impacts of these packaging components are relatively small. Packaging for corrugated board products amounts to relatively small inputs of tape, wrappings of paper or plastic film, steel bands and pallets used as packaging of the saleable product. Pallets are also used in the logistic operations of the corrugated board industry. However, data on usage of pallets has not been collected. Previous iterations of the study have shown that the reported data on the use of pallets are confusing because of the complexity of the matter. Pallets can be returnable or one-way, only used internally in the plants and produced of wood, plastic or paper/ wood combinations. Previously some plants have reported their use in number of pallets while others have reported in kilogram pallet per tonne net saleable product, making it difficult to produce a meaningful figure.

Allocation to paper grades when a mill produces more than one paper grade

The basic data for raw material and chemical inputs are mainly based on recipes used for the production. When allocation was necessary, this was done according to mass production of the different papers.

MATERIAL OUTPUTS

The main output from the paper mills is of course paper. This includes about 2 kg of cores and plugs per tonne paper, which are considered and weighed as part of the net saleable product. The corrugated board plants produce corrugated board and boxes. The average moisture content of the saleable product is 9.1% for Semichemical Fluting and 7.8% for Kraftliner, 8.0% for Testliner and Wellenstoff, 7-8% for corrugated board. The main saleable by-products from the production of Kraftliner are tall oil and turpentine. These are included in the report.

Residues

All residues are reported as wet weight, separated according to their basic nature. Residues are only reported where they leave the system boundaries (i.e., where they are removed from and managed away from the site). As the mill is considered as a blackbox, energy and emissions associated with managing residues internally (onsite) are included within the gate-to-gate inventory data. From the residues of the recycled paper mills, which are mainly rejects from the pulp preparation, it is estimated that about a third is due to rejected materials that were associated with the previous use of the paper (for example, staples, paper clips, tags, adhesive labels, unrecovered fibres, etc). The remaining two thirds is material that is not in any way associated with the previous use of the paper (for example, foreign items such as textiles, plastic packaging, glass, sand and grit, etc). The majority of the rejects are either sent for energy recovery or for recycling.

Of the categories of waste described for the mills:

- Calcium carbonate is primarily reported as a residue from the production of primary fibre-based paper, less commonly so for the recycled paper grades. The majority of the calcium carbonate residue is recycled or used as a soil improver. Only a small proportion is sent for energy recovery.
- Inorganic ashes are reported as a residue for all paper grades. A significant proportion of this residue stream is recycled or used as a soil improver.
- Green liquor sludge is primarily reported as a residue from the production of primary fibre-based paper, less commonly so for the recycled paper grades. The majority of the green liquor residue is recycled or used as a soil improver.
- Organic primary fibre sludge is primarily reported as a residue from the production of recovered fibre-based paper, less commonly so for the primary fibre paper grades. A significant proportion of the organic primary fibre sludge residue is recycled or used as a soil improver. The rest is sent for energy recovery, with only a small proportion of sent to landfill.
- Lime mud is primarily reported as a residue from the production of primary fibre-based paper, less commonly so for the recycled paper grades. The majority of the lime mud residue is recycled or used as a soil improver.
- Organic biological treatment sludge is reported as a residue for all paper grades. The majority of the organic biological treatment sludge residue is recycled or used as a soil improver.
- The majority of the lubricants and oil residue stream are sent for recycling.

In the life cycle inventory, only the quantity of waste is reported. Further details on the waste management solution applied to each waste stream have been collected but are not published in this report. If such details are required, then users of the dataset are encouraged to contact FEFCO or Containerboard Europe directly to request this information.

Allocation of residues to paper grades when a mill produces more than one paper grade

Data for material outputs are based on measurements. These have to be done because the mills have to pay for landfill and incineration or get paid for residues that are reused or recycled, like lubricants, according to the weight. When allocation was necessary, this was done according to causality or according to the mass of the different papers.

ENERGY INPUT AND OUTPUT

Fuel inputs to the sites have been reported in GJ. The lower calorific heat values have been used to calculate GJ from m^3 or tonnes of fuel. Fossil fuel and biomass fuel have been reported separately. The energy figures for the sites include both energy for process and energy for infrastructure. No attempts have been made to differentiate between these two types of energy usage because process energy dominates (98% or more). Input of electricity into the sites is also reported. The electricity produced at the site itself is not reported. Some mills sell energy externally in the form of electricity, steam or warm water. The production sites are treated as a black box in the database, giving data on inputs and outputs only. Because no information is given about what happens within the box it is not possible to calculate an energy balance with the data in the database. Within this black box, energy is recovered through the burning of black liquor and bark from the wood coming in at production sites for primary fibre-based paper production. Most of the energy used in the process for Kraftliner production comes from internal burning of the black liquor. This inherent energy is not reported as part of the fuel input in the gate-to-gate inventory, although it is reported separately in Table 5. The total energy input for the process for Kraftliner production including the black liquor burning is around 14.7 GJ/tonne. The total energy input for the process of Semi Chemical Fluting production is around 11.7 GJ/tonne. The total energy input for the process of testliner and recycled fluting production is around 6.9 GJ/tonne. Combined heat power generation is applied at most of the production sites for recycled fibre based paper, but not always in the same way. The combined heat power generation can cover all or part of the steam consumption (Figure 12). When it covers only part of the steam consumption, then additional boilers also produce steam. The process always uses more heat (steam) than electricity. Therefore, when the installation

is designed to cover the whole steam consumption more electricity is generated than is needed for the process. The excess of electricity is sold to the public grid. There are two possible ways of treating this excess electricity in an LCA.

a. The production of electricity is an integral part of the paper production: it would not be produced if the paper were not produced. Paper is thus considered as the only "product" of the process. In an LCA this would mean that electricity generation for the public grid is "saved" when an excess of electricity produced at a paper mill is sold to the public grid. Thus environmental inputs and outputs are saved since combined heat power installation produces electricity with a higher efficiency than the public grid.

b. Another possibility is to consider the paper and excess electricity as co-products. Paper and electricity are then both "products" from the process. In an LCA this would require allocation of inputs and outputs to both products.

The reported weighted averages of the fuel consumption and emission to air associated with the paper production are calculated according to method b, as this has become common practice at the mills. This means that the fuel consumption and emissions to air do not include the production of the sold electricity and the amount of the sold electricity is not reported. This was calculated as follows: the fuel consumption and emissions to air associated with the total heat production and the net electricity used on site were allocated to the paper production.

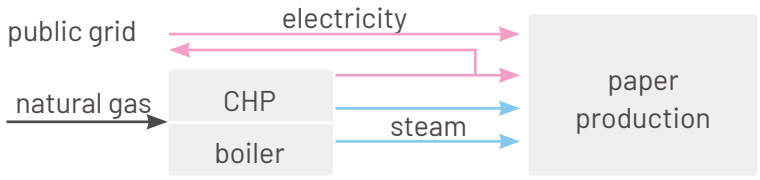


FIGURE 12: CHP, COMBINED HEAT AND POWER GENERATION

Diesel or gasoil/LPG used for internal transports are reported. Most of the energy consumed by the mills producing Kraftliner are by-products from the process and thus originates from the trees i.e. have biomass origin.

Allocation of energy to paper grades when a mill produces more than one paper grade

The energy is measured, because it is paid for. Allocation for fuels and electricity input is calculated according to energy (heat and electricity) required for the production of the different paper grades. Allocation of the other fuels, such as diesel oil used for internal transportation, was calculated according to mass production of each paper grade.

WATER INPUTS AND OUTPUTS

When paper mills use water, they do not consume this water during the production process. After (re)use it is returned to the rivers, lakes or seas as cooling water and purified effluent water. A limited amount of water is evaporated (about 1-1.5 m^3/tonne nsp) in the drying section of the paper production. The water debate focuses on the impact of water consumption. This is best reflected in the local water availability rather than in the amount of water taken into the mills. Therefore, the appropriate indicator is the net difference of water taken in and water returned to the rivers or lakes (water consumed, not taken in). For papers manufactured using virgin fibres (i.e., kraftliner and semi-chemical fluting) a significant quantity of water also enters the process within the pulpwood. This volume of water is not recorded as an input in the inventory and this should be borne in mind when considering the water balance for these paper grades.

TRANSPORT

The transport distances of wood raw materials from the harvesting sites in the forests to the mills have been reported separately for trucks, rail and ships. The trucks and rail wagons are normally loaded to full capacity but go back empty. The trucks carry 40-44 tonnes of wood. This information has been collected on a species-species basis for each mill, considering the wet weight of the wood. Data has also been collected for the delivery of saw mill residues and similar sources of fibre. Distances and tonnages of wood delivered have then been used to calculate the total t.km for delivery of wood by each mode of transport (truck, rail and boat). This is then used to calculate the t.km/t of production for each grade (Kraftliner, Semi Chemical Fluting and Recycled Fluting and Testliner) at each mill, calculated on a mill-by-mill, input-by-input basis. A weighted average t.km is then calculated based on the relative production share of each mill. A similar approach is applied for calculating the transport requirements for recovered paper. Transport distances from point of origin of the recovered paper bales to the mills have been reported on a recovered paper grade-by-grade basis for each mill. Distances and tonnages of recovered paper delivered have then been used to calculate the total t.km for delivery of recovered paper by each mode of transport (truck, rail and boat). This is then used to calculate the t.km/t of production for each grade (Kraftliner, Semi Chemical Fluting and Recycled Fluting and Testliner) at each mill, calculated on a mill-by-mill, input-by-input basis. A weighted average t.km is then based on the relative production share of each mill. Generally, the lorries are loaded to full capacity. Assuming this is transported by a truck with a loading capacity of 40 tonnes this means that this figure has to be used in combination with data on inputs and outputs for transport by a 40t truck. Transport of the residues was not included in the questionnaire as this was seen to be part of the residue treatment. During the discussions with the technical experts it became clear that the transport of rejects is mainly to nearby landfill, 3-30 km. Data was also collected from the papermills on average delivery distances and modes of transports to their customers. This data was provided on a product-by-product basis and was used to calculate a weighted average t.km for delivery of paper to the corrugated board plants. However, any one corrugating plant will of course source the substrates they use from many different suppliers. Therefore, the values presented in the inventory are only indicative and in practice users of the data may wish to consider delivery of materials on a case-by-case.

Internal transport is included in the energy input.

EMISSIONS TO AIR

Emissions from fuel combustion (transport, electricity generation for the public grid) outside the mill are not included in the data. In case the site sold electricity, the emissions associated with the sold electricity are not included. Emissions to air from the mills have been reported. For dust, TRS (H2S), NOx and SOx the figures from the paper mills are mostly based on measurements. For CO_2 the figures reported for the mills are based on emissions reported to authorities where provided, or where these were not provided they are based on calculations and reported separately for fossil and biomass origin. Corrugated board plants have no measured air emission data to report. Therefore, the CO_2 emission figures for corrugated board production reported in Table 4 and in the Annex are calculated from reported figures for consumption of different fuels in the corrugated board plants. The emission factors in Table 3 were used for the calculations. For other emissions to air from the corrugated board plants, these have been calculated considering production of heat using the corresponding fuels sources, using emission factors from Ecoinvent 3.11.

TABLE 3 DEFAULT FACTORS FOR CALCULATING CO_2 EMISSIONS TO AIR FROM COMBUSTION OF FUELS

FUEL	KG FOSSIL CO_2 PER GJ	KG BIOGENIC CO_2 PER GJ	SOURCE
Natural gas	56.2	-	Natural gas - UK Government GHG Conversion Factors for Company Reporting 2024
Heavy fuel oil	78.9	-	Fuel oil - UK Government GHG Conversion Factors for Company Reporting 2024
Light fuel oil	73.5	-	Diesel (100% mineral diesel) - UK Government GHG Conversion Factors for Company Reporting 2024
Diesel oil	73.5	-	Diesel (100% mineral diesel) - UK Government GHG Conversion Factors for Company Reporting 2024
LPG propane	64.5	-	Propane - UK Government GHG Conversion Factors for Company Reporting 2024
Hard coal/coke	93.5	-	Coal (industrial) - UK Government GHG Conversion Factors for Company Reporting 2024
Brown coal (lignite)	101.0	-	Lignite - WRI Emission Factors from Cross Sector Tools March 2017
Brown coal (briquettes)	97.5	-	Brown coal briquettes - WRI Emission Factors from Cross Sector Tools March 2017
Peat	106.0	-	Peat - WRI Emission Factors from Cross Sector Tools March 2017
Wood and wood chips	-	112.0	Wood or Wood waste - WRI Emission Factors from Cross Sector Tools March 2017
Bark	-	112.0	Wood or Wood waste - WRI Emission Factors from Cross Sector Tools March 2017
Black liquor	-	95.3	Sulphite lyes (Black liquor) - WRI Emission Factors from Cross Sector Tools March 2017
Biogas	-	54.6	Other biogas - WRI Emission Factors from Cross Sector Tools March 2017
Sludge	-	54.6	Sludge gas - WRI Emission Factors from Cross Sector Tools March 2017
Refuse derived fuel (RDF) – fossil fraction	91.7	-	Municipal waste (Non biomass fraction) - WRI Emission Factors from Cross Sector Tools March 2017
Refuse derived fuel (RDF) – biogenic fraction	-	100.0	Municipal wastes (Biomass fraction) - WRI Emission Factors from Cross Sector Tools March 2017

Emissions to air in the flue gas from the CHP the power station are given for the mills producing testliner and recycled fluting that use combined heat power generation. Emissions from the incineration of rejects with energy recovery at the mill are included. Emissions in the steam from the drying section of the paper machines are not included. When mills have anaerobic wastewater treatment on the site, biogas originating from this process is used as a fuel by the mill. The emissions to air originating from the use of biogas as fuel are included.

Very few mills were able to report any figures for emissions such as metals etc. Where data was reported the same substances were not always covered and where common emissions were reported these showed a large


variation per mill, primarily due to differences in measuring/monitoring and/or calculation regimes. Therefore, this information has not been included in the datasets. For conducting their own LCI or LCA studies, users of the dataset are advised that they should include such emissions. These can be estimated through the application of standard emissions data for the combustion of different fossil fuels, together with the amount of fossil fuels used in the processes (as indicated in Table 4 and the Annex). This will allow an estimation to be made of the order of magnitude of these emissions.

Allocation of emissions to paper grades when a mill produces more than one paper grade

Emissions to air are calculated from measurements, applied technology, permit values or from the input of fuels. Necessary allocations were done in the same way as for energy input.

EMISSIONS TO WATER

Water that is taken in must be treated before it is used in the process, and it is again treated after the process before it is released as effluent to a recipient. The substances in the effluent after wastewater treatment are reported. All mills have some sort of effluent water treatment, either mechanical treatment by sedimentation or in addition biological anaerobic and aerobic or chemical treatment of the effluent. A few mills send their effluent water to an external communal treatment plant. The volume of effluent water is reported separately for treated process water and thermally polluted effluent (e.g. cooling water). All mills have reported the figures for outgoing effluent water to the recipient i.e. effluent water after final treatment. The amount of substances (COD, BOD, suspended solids) per m^3 of effluent from the different mills show very little variation when the efficiency of the waste water treatment station is the same. The amount of substances per tonne paper production may however vary according to the amount of effluent, depending on specific circumstances in the paper production process in the different mills. In the questionnaire for data collection, a number of other emissions were asked for such as oils, nitrates, acids, AOX, chlorate, chlorides, borates, phenol, Hg, Pb etc. Few mills were able to report figures, probably because there are no or few measurements. Only COD, BOD5, suspended solids, total nitrogen and total phosphorus are based on data from most mills in addition to the total volume of effluent waters. Due to the water treatment it is possible that the content of certain substances per m^3 is higher in the water is taken in from a river than in the effluent released into the river. In an LCA this would mean that the production of paper could be credited for the reduction in substances, although in practice this rarely happens. This principle is illustrated in Figure 13.

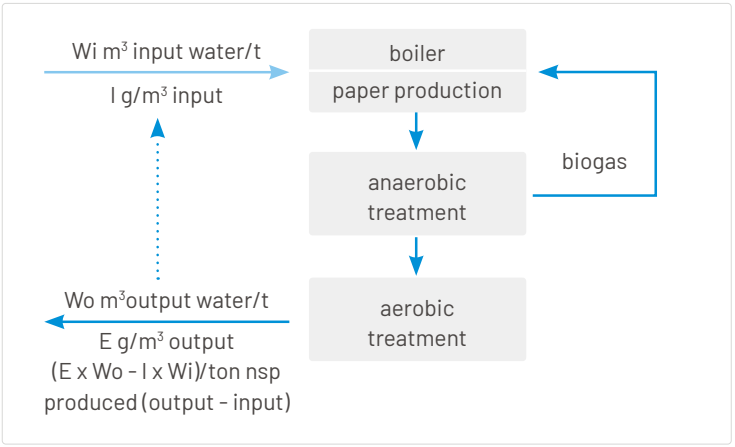

Wi: input water in m^3
Wo: output water in m^3 (effluent)
I: amount of substances in input water
E: amount of substances in output water

FIGURE 13: POTENTIAL CREDIT FOR REDUCTION OF SUBSTANCES IN THE EFFLUENT WATER

Since only a few mills analyse their incoming water the available data cannot be considered as representative. Therefore, only data for the emissions to the recipient are given, without taking into account the substances in the incoming water. Most of the corrugated board plants have internal wastewater treatment that can be treated externally afterwards. In case the wastewater is not further treated externally and released to the environment, the emission level of substances is so low that reporting them is not required by authorities.

The reported data are therefore based on a small sample. Besides the substances reported in Table 4 and the Annex, very few plants have also given data on some of the following emissions: metals (Cadmium, Chromium, Lead, Nickel, Iron, Boron, Aluminium), AOX, Chlorine and Phosphorus. The amounts are below 0.001 kg/tonne nsp.

Allocation of emissions to paper grades when a mill produces more than one paper grade

As far as waterborne emissions per m^3 are measured for a mill, these data are well documented. The figures reported are usually based on continuous measurements according to control programmes set by official authorities. Given emissions to water are measured according to standard methodology. Where necessary, allocation between paper grades is done according to mass of produced paper grade. The water used for the production of White Top Testliner is relatively higher than for Brown Testliner and Recycled Fluting. No separate data are reported as the effluent from its production is mixed with that from the production of other grades produced on site. Data on emissions to water from the corrugated plants were also collected. However, the corrugated plants are not subject to Industrial Emissions legislation, and therefore the quantity and quality of available data is inconsistent. This is further complicated by the fact that the corrugated plants do not all have their own effluent treatment facilities or treat only certain aspects of the wastewater associated with specific processes (for example, ink recovery). Many plants discharge a proportion of their wastewater under specific agreement to public effluent treatment facilities and therefore do not have access to data on the releases to the environment (after final treatment). It did not prove possible to make a reliable analysis with the data collected during the latest survey. For this reason, data representative of emissions after a public waste water treatment plant should be considered for the waste emissions from the corrugated plant.



DATA

COVERAGE AND COMPARABILITY OF THE DATASETS OVER TIME

Containerboard Europe and FEFCO have regularly surveyed the environmental performance of the corrugated industry for more than 27 years. This is the eleventh edition of the report. Inevitably, over time the coverage of the surveys has changed:

- Old paper mills and converting facilities have closed and new mills and converting facilities have opened
- Additional mills and converting facilities have opted to participate in the survey, increasing the coverage and representativeness of the datasets

Over the years there has been increased participation in the survey, which means that the weighted averages generated are more representative of average European production and therefore represent an improvement in the quality of the datasets over time. However, it also means that comparing the weighted averages across the surveys is must be done with care. Trends may be obscured by changes in participation in the surveys. The weighted average results presented in this edition of the report should therefore not be compared directly with the weighted average results in the previous editions of the report without fully appreciating the changes in participation.

Furthermore, lightweighting efforts mean that corrugated base paper base weights (measured in grams per square metre) have been reduced over time. The effect of these lightweighting efforts mean that energy consumption per tonne of production will not decrease at the same rate as energy consumption per square metre of production (and in some survey years energy consumption per tonne may even show an increase compared to the previous survey, despite more energy efficient production per square metre).

Furthermore, there is a continued drive to improve recycled fibre quality and an increase in sizing and coated papers, which may also contribute additional energy demands per tonne of production. As the papermill is considered as a black box, it is not possible to ascertain how much this trend has influenced the results of the life cycle inventory, but this qualitative information provides some context to some of the results achieved and trends observed over time.

RELATIONSHIP TO THE PRODUCT ENVIRONMENTAL FOOTPRINT (PEF)

Containerboard Europe and FEFCO have been compiling the environmental database for the European corrugated industry for more than twenty-seven years. Over the course of multiple iterations of the project a robust process has been developed in which the data provided is processed and checked by both LCA practitioners and industry experts. The process and data are then subjected to an independent peer review.

This experience has led to the generation of a well-respected and transparent life cycle inventory dataset for the production of corrugated base papers and the conversion of these base papers into corrugated board and corrugated boxes. Therefore, Containerboard Europe and FEFCO intend to continue to collect and process the data using the same methods and present the information in the same format.

More recently, the European Commission has proposed the Product Environmental Footprint (PEF) as a common way of measuring environmental performance[9]. To facilitate the adoption of the PEF methodology, the European Commission is developing a database of life cycle inventory data. Category rules for compiling life cycle studies in compliance with the PEF methodology are also in development. PEF category rules have already been published for Intermediate Paper Products[10], but no category rules have been published covering the conversion of these into end products.

9 https://eplca.jrc.ec.europa.eu/EnvironmentalFootprint.html?msclkid=d1c44024bd6311ec9a31602979545205
10 Product Environmental Footprint Category Rules: Intermediate Paper Products, CEPI, October 2018

The PEF methodology and the PEF database are still in development and open to discussion, and category rules are currently only available for the production of base papers not including conversion. Therefore, whilst the data for this life cycle inventory has been collected with reference to the PEF and, where relevant, the Product Category rules for Intermediate Paper Products, no claim of compliance with the PEF methodology or data requirements is made.



RESULTS

LIFE CYCLE INVENTORY FOR CORRUGATED BOARD 2024

Table 4 shows the calculated inputs and outputs for the production of 1 tonne of corrugated board products in Europe with an average corrugated base paper composition. The production of corrugated board is normally expressed in m^2. However, for LCA it is preferable to have it expressed in weight.

For the average corrugated board product, the paper input is 1.12 tonnes/tonne corrugated board, with an output of 0.12tonnes paper for recycling.

The original five datasets for the four main paper grades and corrugated board/box production from which the data are derived, are reported in the Annex. The data for the corrugated box is calculated by multiplying the average paper grade composition by 1.12 and adding the corrugated board/box data reported in the Annex.

TABLE 4: LIFE CYCLE INVENTORY FOR THE PRODUCTION OF 1 TONNE OF CORRUGATED BOXES IN EUROPE, WITH AVERAGE CORRUGATED BASE PAPER COMPOSITION

PRODUCT		2024
	tonne net saleable product	**1**
SOLD BY PRODUCTS		
Tall oil	kg/t	2.51
Tall soap	kg/t	0.67
Turpentine	kg/t	0.19
Bark chips	kg/t	1.30
Wood chips	kg/t	0.33
RAW MATERIAL		
Wood consumption	as bone dry weight (= 45% of transported total wet weight)	
Softwood logs	t/t	0.123
Hardwood logs	t/t	0.036
Sawmill residues softwood	t/t	0.017
Sawmill residue hardwood	t/t	0.001
Total wood	*t/t*	*0.177*
Recovered paper	as wet weight	1.048
Category		
Mixed grades	t/t	0.464
Corrugated and Kraft, pre-consumer	t/t	0.083
Corrugated and Kraft, post-consumer	t/t	0.476
Newspaper and Magazines	t/t	0.006
Other grades	t/t	0.019
Purchased pulp consumption	as bone dry weight	
Bleached pulp	t/t	0.0139

Unbleached pulp	t/t	0.0019
Pulp from paper for recycling	t/t	0.0005
Paper consumption for corrugated board production		
Total	t/t	1.12
TRANSPORT OF RAW MATERIALS		
Wood		
Wood with truck	t.km/t	45
Wood with rail	t.km/t	25
Wood with boat (sea)	t.km/t	45
Wood with boat (inland barge)	t.km/t	10
Recovered paper		
Recovered paper with truck	t.km/t	334
Recovered paper with rail	t.km/t	29
Recovered paper with boat (sea)	t.km/t	73
Recovered paper with boat (inland barge)	t.km/t	0
Recovered paper with boat (Ro-Ro ferry)	t.km/t	12
Purchased pulp		
Purchased pulp with truck	t.km/t	4
Purchased pulp with rail	t.km/t	1
Purchased pulp with boat (sea)	t.km/t	51
Purchased pulp with boat (inland barge)	t.km/t	0
Non-fibre inputs		
Non-fibre with truck	t.km/t	23
Non-fibre with rail	t.km/t	0
Non-fibre with boat (sea)	t.km/t	8
Non-fibre with boat (inland barge)	t.km/t	1
Paper to corrugated board plants*		
Paper with truck	t.km/t	525
Paper with rail	t.km/t	207
Paper with boat (sea)	t.km/t	243
Paper with boat (inland sea)	t.km/t	26
ENERGY INPUTS		
Steam	GJ/t	0.421
Bought electricity	GJ/t	1.431
Fossil fuels		
Natural gas	GJ/t	3.839
Heavy fuel oil	GJ/t	0.032
Light fuel oil	GJ/t	0.049
Diesel oil	GJ/t	0.007
LPG	GJ/t	0.027

Coal	GJ/t	0.114
Lignite	GJ/t	0.022
Peat	GJ/t	0.026
Total fossil fuels	*GJ/t*	*4,116*
Renewable fuels (biofuels)		
Bark	GJ/t	0.345
Wood (scrap wood, wood pellets, saw dust)	GJ/t	0.482
Tall oil/pitch oil	GJ/t	0.020
Other biofuels	GJ/t	0.003
Total renewable fuels	*GJ/t*	*0.850*
Refuse derived fuel	GJ/t	0.633
Total fuel	*GJ/t*	*5.551*
WATER		
Input total	m^3/t	13.74
Ground water (non-renewable)	m^3/t	0.00
Ground water (renrewable)	m^3/t	2.44
Surface water - lake	m^3/t	3.06
Surface water - river	m^3/t	7.58
Municipal water	m^3/t	0.56
Rainwater	m^3/t	0.09
Other water received	m^3/t	0.00
Water in – water out	*m^3/t*	*1.85*

PROCESS CHEMICALS AND ADDITIVES, DRY MASS		
Alum (Al2(S04)3	kg/t	1.94
Biocides	kg/t	0.095
Borax	kg/t	0.13
$CaCO_3$	kg/t	5.97
Ground Calcium Carbonate	*kg/t*	*4.59*
Precipitated Calcium Carbonate (purchased)	*kg/t*	*1.37*
CaO, calcium oxide (lime)	kg/t	0.56
Coagulants	kg/t	0.16
Colourants	kg/t	0.44
CO_2, carbon dioxide	kg/t	0.64
CO_2, compressed gaseous form	*kg/t*	*0.27*
CO_2, liquid form	*kg/t*	*0.37*
Defoamer	kg/t	0.058
Fillers (clay, kaolin)	kg/t	1.26
Flocculants	kg/t	0.12
Glue, cold and hot melts	kg/t	1.33
H_2O_2, peroxide	kg/t	0.27

H_2SO_4, sulphuric acid	kg/t	1.18
H_3PO_4, phosphoric acid	kg/t	0.019
Water-based ink for flexo printing	kg/t	2.66
Varnish for printing	kg/t	0.65
Ligno sulphonate	kg/t	0.70
Lubricants	kg/t	0.022
MgO, magnesium oxide	kg/t	0.0091
$NaClO_3$, sodium chlorate	kg/t	0.22
Na_2CO_3, sodium carbonate (soda)	kg/t	0.069
Na_2SO_4, sodium sulphate	kg/t	0.073
NaOH, sodium hydroxide	kg/t	2.18
NH_3, ammonia	kg/t	0.039
Oxygen, O_2	kg/t	0.54
O_2, compressed gaseous form	*kg/t*	*0.49*
O_2, liquid form	*kg/t*	*0.05*
Pitch dispergents	kg/t	0.012
Polymer and retention agents	kg/t	0.31
S, sulphur	kg/t	0.16
Sizing agents	kg/t	0.193
AKD sizer (alkyl ketene dimer)	*kg/t*	*0.118*
ASA sizer (alkenyl succinic anhydride)	*kg/t*	*0.049*
Rosin	*kg/t*	*0.025*
SO_2, sulphur dioxide	kg/t	0.00
Talc, malusil	kg/t	0.0042
Urea	kg/t	0.24
Starch, corn (including modified and cationic starch from corn)	kg/t	19.08
Starch, potato (including modified and cationic starch from potato)	kg/t	11.08
Starch, wheat (including modified and cationic starch from wheat)	kg/t	25.35
Starch, other (flour, pea, undefined)	kg/t	12.80

EMISSIONS TO AIR		
Particulates, <2.5µm	kg/t	0.0073
Particulates, >2.5µm and <10µm	kg/t	0.0041
Particulates, >10µm	kg/t	0.0201
CO_2 (fossil)	kg/t	260.46
CO_2 (biomass)	kg/t	299.04
CO	kg/t	0.27
NOx (as NO_2)	kg/t	0.32
SOx (as SO_2)	kg/t	0.10

TRS (H_2S as S)	kg/t	0.0034
EMISSIONS TO WATER		
Water output	m^3/t	
Thermally polluted water – cooling water to freshwater	m^3/t	2.32
Thermally polluted water – cooling water to seawater	m^3/t	0.75
Process water to off-site wastewater treatment	m^3/t	1.36
Process water to freshwater after treatment onsite wastewater treatment	m^3/t	5.87
Process water to seawater after treatment onsite wastewater treatment	m^3/t	1.57
Total water out	m^3/t	11.88
Waterborne emissions – freshwater		
COD	kg/t	1.18
BOD5	kg/t	0.22
TOC	kg/t	0.21
Suspended solids	kg/t	0.22
Total Nitrogen	kg/t	0.067
AOX	kg/t	0.0021
Total Phosphorous	kg/t	0.0054
Waterborne emissions – seawater		
COD	kg/t	0.35
BOD5	kg/t	0.054
TOC	kg/t	0.056
Suspended solids	kg/t	0.056
Total Nitrogen	kg/t	0.015
AOX	kg/t	0.0003
Total Phosphorous	kg/t	0.0017
RESIDUES	**wet weight**	
Calcium carbonate	kg/t (75% dry content)	0.074
Ink residues	kg/t (50% dry content)	0.355
Inorganic ashes (10 01 01)	kg/t (85% dry content)	9.49
Green liquor sludge	kg/t (32% dry content)	1.48
Organic primary fibre sludge	kg/t (43% dry content)	20.17
Lime mud	kg/t (32% dry content)	1.70
Organic biological treatment sludge	kg/t (43% dry content)	18.41
Bark and wood	kg/t (45% dry content)	0.034
Paper for recycling	kg/t (90% dry content)	120.00
Rejects - total	kg/t (57% dry content)	46.58
*Rejects, paper related***	*kg/t (57% dry content)*	*15.51*
*Rejects, other****	*kg/t (57% dry content)*	*31.02*
Starch, glue (wet weight)	kg/t (30% dry content)	0.102
Lubricants and oil	Kg/t	0.081

«0.00» no input or below reporting requirements see «chemical input»

«na» not available

*As this life cycle inventory is intended to be representative of average European production, only transport from European paper mills to European corrugated board production sites has been considered in the weighted average. Transport associated with export of paper outside of Europe has not been considered

**Rejected materials that were associated with the previous use of the paper (for example, staples, paper clips, tags, adhesive labels, unrecovered fibres, etc)

***Material that is not in any way associated with the previous use of the paper (for example, foreign items such as plastic packaging, glass, sand and grit, etc)



ADDITIONAL INFORMATION ON ENERGY AND FUELS

INTERNAL FUELS

The energy inputs presented in Table 4 and in the life cycle inventories detailed in the Annex refers only to external fuels supplied to the process. However, many papermills also produce their own internal fuels as a by-product of the pulping processes or from the management of waste streams. In particular, the following are the main internal fuels relevant to the papermaking process:

- Black liquor – a by-product from the kraft process when digesting pulpwood into paper pulp. It is an aqueous solution of lignin residues, hemicellulose, and the inorganic chemicals used in the process
- Bark – from the debarking process
- Biogas and biosludge – from the wastewater treatment process
- Refuse-derived fuel – from the processed rejects from processing of paper for recycling

The consumption of all fuels and energy (purchased fuels and electricity and internal fuels) for each of the corrugated paper grades is summarised in Table 5. This data is for information purposes only and should not be added to the life cycle inventory for each paper grade as it refers to fuels that are generated and consumed within the "black box" of the papermill. The internal fuels will be used for production of heat (in the form of steam) and electricity at the mill.

TABLE 5: EXTERNAL ENERGY INPUTS AND INTERNAL FUELS CONSUMED FOR THE PRODUCTION OF CORRUGATED BASE PAPERS

		Semi chemical fluting production	Kraftliner production	Recycled fluting production	Testliner production
EXTERNAL ENERGY INPUTS					
Steam	GJ/t	0.000	0.000	0.790	0.790
Bought electricity	GJ/t	1.246	1.509	0.861	0.861
External fuels	GJ/t	3.075	2.826	4.338	4.338
Total external energy inputs	**GJ/t**	**4.321**	**4.335**	**5.989**	**5.989**
INTERNAL FUELS					
Black liquor	GJ/t	5.379	8.236	0.197	0.197
Bark	GJ/t	1.185	1.793	0.058	0.058
Biogas and biosludge	GJ/t	0.070	0.055	0.338	0.338
Refuse derived fuel (RDF)*	GJ/t	0.000	0.048	0.251	0.251
Other internal fuels	GJ/t	0.275	0.226	0.022	0.022
Total internal fuels	**GJ/t**	**7.453**	**10.358**	**0.863**	**0.863**
TOTAL ENERGY (BOUGHT ELECTRICITY, PURCHASED STEAM, EXTERNAL FUELS, INTERNAL FUELS)					
Total energy	**GJ/t**	**11.744**	**14.693**	**6.852**	**6.852**

*RDF FROM REJECTS FROM PAPER FOR RECYCLING – ESTIMATED AS ~60% FOSSIL AND ~40% BIOGENIC IN CONTENT

SUSTAINABLE FOREST MANAGEMENT

There is currently no life cycle impact assessment methodology for biodiversity impacts of forest management to produce primary fibres for fibre-based products. Nevertheless, biodiversity impacts are an essential element of forest industry products. Sustainable forest management practices have been developed to protect and maintain the ecosystem services in managed forests and plantations. The voluntary sustainable forest management certification schemes have been designed to address relevant practices that help protect ecosystem services such as biodiversity or those that are impacted by land use and their implementation has been verified through an accredited, independent third party. These practices set a proxy for mitigating land use impacts and protecting biodiversity.

The data collection revealed that more than 80% of the pulp wood used for the production of corrugated base papers by the companies returning the survey was chain of custody certified under a forest management system, i.e., being sourced from sustainably managed forests. Predominantly, primary fibres are FSC or PEFC chain of custody certified.

Details of the specific countries of origin and species of wood used are not provided in this report.

PEER REVIEW

The study presented in this report has been subject to a peer review by ifeu - Institute for Energy and Environmental Research Heidelberg GmbH. The peer review concludes that:

- the methods used to compile the database are scientifically and technically valid, and consistently used.
- the data used are appropriate and reasonable in relation to the goal of the LCA database.
- the LCA database report is transparent and consistent.

The full peer review statement is available as Annex 2 of this report.

DEFINITIONS

ALLOCATION
Technique used in life cycle assessment for partitioning the inputs and outputs of a system amongst products.

CONVERTED CORRUGATED BOX
The corrugated board that is ready to use as a box. All shavings are accounted for.

EFFLUENT
Water leaving the mill after treatment.

INCINERATION + ENERGY
Incineration of residues with energy recovery.

FLUTING
Paper grades used for the corrugated layer of corrugated board.

FUNCTIONAL ADDITIVES
Additives that influence the properties of paper.

LINER
Paper grades used for the surface layer of corrugated board.

LIFE CYCLE ASSESSMENT (LCA)
Compilation and evaluation of the inputs, outputs and the potential environmental impacts of a product system throughout its life cycle.

LIFE CYCLE IMPACT ASSESSMENT
Phase of the life cycle assessment aimed at understanding and evaluating the magnitude and significance of the potential environmental impacts of a product system.

LIFE CYCLE INVENTORY ANALYSIS
Phase of the life cycle assessment involving compilation, and the quantification of inputs and outputs, for a given product system throughout its life cycle.

PACKAGING MATERIALS
Materials bought and used for the packaging of the saleable product (wrappings, pallets).

PAPER FOR RECYCLING
Paper collected for repulping at a papermill to produce papers containing recycled fibres. Paper for recycling may originate from pre-consumer sources (e.g., process waste) or post-consumer sources

PRIMARY FIBRE
Virgin fibre, fibres that have not been recycled before use in paper production.

PROCESS ADDITIVES
Additives that are used to guarantee that the process of paper production runs smoothly or to increase the production.

REJECTS
Material in recovered paper, which is eliminated during pulp preparation.

SHAVINGS
The total of all base paper cuttings that do not end up in the converted corrugated box (e.g. from corrugator trimmings, die-cuttings). Shavings are 100% recycled.

TONNE NSP (NET SALEABLE PRODUCT)
1 tonne of paper/corrugated board product sold to the customer, including core plugs for the paper.

TRANSPORT DISTANCE OF RECOVERED PAPER
Distance from recovered paper supplier to the paper mill.

TRANSPORT DISTANCE OF WOOD
Distance from harvesting site to the paper mill.

RECYCLED FLUTING
Recovered fibre-based Fluting

RECOVERED FIBRES
Fibres produced from recycled paper ready for use in paper production

ANNEX 1

GATE-TO-GATE INVENTORIES FOR CORRUGATED BASE PAPERS AND CORRUGATED CONVERTING PROCESSES

			Semi chemical fluting production	Kraftliner production	Recycled fluting production	Testliner production	Corrugated board production
PRODUCT	**TONNE NET SALEABLE PRODUCT**		**1**	**1**	**1**	**1**	**1**
SOLD BYPRODUCTS							
Tall oil		kg/t	7.71	13.27	0.38	0.38	NA
Tall soap		kg/t	1.98	1.29	0.46	0.46	NA
Turpentine		kg/t	0.39	0.86	0.06	0.06	NA
Bark chips		kg/t	0.00	8.63	0.00	0.00	NA
Wood chips		kg/t	0.00	2.17	0.00	0.00	NA
RAW MATERIAL							
Wood consumption		as bone dry weight (= 45% of transported total wet weight)					
Softwood pulpwood		t/t	0.000	0.720	0.0147	0.0147	NA
Hardwood pulpwood		t/t	0.801	0.134	0.0004	0.0004	NA
Sawmill residues softwood		t/t	0.005	0.092	0.0029	0.0029	NA
Sawmill residue hardwood		t/t	0.059	0.000	0.000	0.000	NA
Total wood		*t/t*	*0.865*	*0.946*	*0.0180*	*0.0180*	*NA*
Recovered paper		as wet weight	0.1001	0.2871	1.0569	1.0569	NA
Category							
Mixed grades		t/t	0.0391	0.0986	0.4722	0.4722	NA
Corrugated and Kraft, pre-consumer		t/t	0.0100	0.0199	0.0846	0.0846	NA
Corrugated and Kraft, post-consumer		t/t	0.0508	0.1685	0.4742	0.4742	NA
Newspaper and Magazines		t/t	0.0000	0.0000	0.0061	0.0061	NA
Other grades		t/t	0.0001	0.0001	0.0200	0.0200	NA
Purchased pulp consumption		as bone dry weight					
Bleached virgin pulp		t/t	0.0000	0.0881	0.0006	0.0006	NA
Unbleached virgin pulp		t/t	0.0139	0.0097	0.0002	0.0002	NA
Pulp from paper for recycling		t/t	0.0000	0.0000	0.0005	0.0005	
Paper consumption for corrugated board production							
Total		t/t	NA	NA	NA	NA	1.120

TRANSPORT OF RAW MATERIALS						
Wood						
Wood with truck	t.km/t	225	247	4	4	NA
Wood with rail	t.km/t	170	135	1	1	NA
Wood with boat (sea)	t.km/t	0	282	2	2	NA
Wood with boat (inland barge)	t.km/t	317	27	0	0	
Recovered paper						
Recovered paper with truck	t.km/t	37	93	336	336	NA
Recovered paper with rail	t.km/t	0	67	20	20	NA
Recovered paper with boat (sea)	t.km/t	0	0	77	77	NA
Recovered paper with boat (inland barge)	t.km/t	0	0	0	0	NA
Recovered paper with boat (Ro-Ro ferry)	t.km/t	0	0	13	13	NA
Purchased pulp						
Purchased pulp with truck	t.km/t	25	20	0	0	NA
Purchased pulp with rail	t.km/t	0	6	0	0	NA
Purchased pulp with boat (sea)	t.km/t	93	261	10	10	NA
Purchased pulp with boat (inland barge)	t.km/t	0	1	0	0	NA
Non-fibre inputs						
Non-fibre with truck	t.km/t	57	57	14	14	NA
Non-fibre with rail	t.km/t	0	0	0	0	NA
Non-fibre with boat (sea)	t.km/t	5	44	1	1	NA
Non-fibre with boat (inland barge)	t.km/t	0	7	0	0	NA
Paper to corrugated board plants*						
Paper with truck	t.km/t	NA	NA	NA	NA	468
Paper with rail	t.km/t	NA	NA	NA	NA	185
Paper with boat (sea)	t.km/t	NA	NA	NA	NA	217
Paper with boat (inland barge)	t.km/t	NA	NA	NA	NA	23
ENERGY INPUTS						
Steam	GJ/t	0.000	0.000	0.405	0.405	0.037
Bought electricity	GJ/t	1.246	1.509	0.773	0.773	0.446
Fossil fuels						
Natural gas	GJ/t	0.053	0.791	2.982	2.982	0.890
Heavy fuel oil	GJ/t	0.199	0.100	0.010	0.010	0.004
Light fuel oil	GJ/t	0.071	0.088	0.013	0.013	0.022
Diesel oil	GJ/t	0.002	0.004	0.007	0.007	0.000
LPG	GJ/t	0.000	0.033	0.001	0.001	0.021
Coal	GJ/t	0.000	0.008	0.107	0.107	0.011
Lignite	GJ/t	0.000	0.000	0.023	0.023	0.000

Peat	GJ/t	1.389	0.0003	0.000	0.000	0.000
Total fossil fuels	*GJ/t*	*1.715*	*1.025*	*3.090*	*3.090*	*0.949*
Renewable fuels (biofuels)						
Bark	GJ/t	0.048	0.947	0.212	0.212	0.0000
Wood (scrap wood, wood pellets, saw dust)	GJ/t	1.270	0.691	0.372	0.372	0.0002
Tall oil/pitch oil	GJ/t	0.000	0.115	0.003	0.003	0.0000
Other biofuels	GJ/t	0.041	0.000	0.002	0.002	0.0000
Total renewable fuels	*GJ/t*	*1.360*	*1.753*	*0.588*	*0.588*	*0.0002*
Refuse derived fuel*	GJ/t	0.0002	0.047	0.660	0.660	0.000
Total fuel	*GJ/t*	*3.075*	*2.826*	*4.338*	*4.338*	*0.950*
WATER						
Input total	m^3/t	50.78	31.51	8.07	8.07	0.35
Ground water (non-renewable)	m^3/t	0.00	0.00	0.00	0.00	0.00
Ground water (renewable)	m^3/t	0.00	0.21	2.45	2.45	0.08
Surface water – lake	m^3/t	44.04	9.92	0.76	0.76	0.00
Surface water – river	m^3/t	6.74	21.06	4.49	4.49	0.01
Surface water - sea	m^3/t	0.00	0.00	0.00	0.00	0.00
Municipal water	m^3/t	0.00	0.06	0.31	0.31	0.26
Rainwater	m^3/t	0.00	0.24	0.06	0.06	0.00
Other water received	m^3/t	0.00	0.00	0.00	0.00	0.00
Water in – water out	*m^3/t*	*5.91*	*3.04*	*1.16*	*1.16*	*0.18*

*EXTERNALLY SUPPLIED RDF – ESTIMATED AS ~60% FOSSIL AND ~40% BIOGENIC IN CONTENT

PROCESS CHEMICALS AND ADDITIVES, DRY MASS						
Alum (Al2(SO4)3	kg/t	0.00	1.21	0.012	0.012	NA
Binders (synthetic latex)	kg/t		1.05			
Biocides	kg/t	0.12	0.11	0.08	0.08	NA
Borax	kg/t	NA	NA	NA	NA	0.13
$CaCO_3$	kg/t	0.00	26.34	2.09	2.09	NA
Ground Calcium Carbonate	*kg/t*	*0.00*	*20.71*	*1.54*	*1.54*	*NA*
Precipitated Calcium Carbonate (purchased)	*kg/t*	*0.00*	*5.63*	*0.55*	*0.55*	*NA*
CaO, calcium oxide (lime)	kg/t	0.01	3.57	0.025	0.025	NA
Coagulants	Kg/t	1.40	0.10	0.12	0.12	NA
Colourants	kg/t	0.00	0.062	0.45	0.45	NA
CO_2, carbon dioxide	kg/t	0.00	3.71	0.08	0.08	NA
CO_2, compressed gaseous form	*kg/t*	*0.00*	*1.76*	*0.00*	*0.00*	*NA*
CO_2, liquid form	*kg/t*	*0.00*	*1.95*	*0.08*	*0.08*	*NA*
Defoamer	kg/t	0.18	0.11	0.04	0.04	NA
Fillers (clay, kaolin)	kg/t	0.00	7.42	0.15	0.15	NA
Flocculants	Kg/t	0.12	0.14	0.10	0.10	NA

Glue, cold and hot melts	kg/t	NA	NA	NA	NA	1.33
H_2O_2, peroxide	kg/t	0.00	1.81	0.00	0.00	NA
H_2SO_4, sulphuric acid	kg/t	0.052	7.28	0.079	0.079	NA
H_3PO_4, phosphoric acid	kg/t	0.024	0.034	0.014	0.014	NA
Water-based ink for flexo printing	kg/t	NA	NA	NA	NA	2.66
Varnish for printing	kg/t	NA	NA	NA	NA	0.65
Ligno sulphonate	kg/t	0.00	0.00	0.74	0.74	NA
Lubricants	kg/t	0.053	0.14	0.000	0.000	NA
MgO, magnesium oxide	kg/t	0.48	0.00	0.00	0.00	NA
$NaClO_3$, sodium chlorate	kg/t	0.00	1.44	0.00	0.00	NA
Na_2CO_3, sodium carbonate (soda)	kg/t	3.52	0.00	0.002	0.002	NA
Na_2SO_4, sodium sulphate	kg/t	0.00016	0.48	0.00	0.00	NA
NaOH, sodium hydroxide	kg/t	14.48	8.43	0.40	0.40	0.25
NH_3, ammonia	kg/t	0.52	0.19	0.0001	0.0001	NA
Oxygen, O_2	kg/t	0.00	3.24	0.05	0.05	NA
O_2, compressed gaseous form	*kg/t*	*0.00*	*3.24*	*0.00*	*0.00*	*NA*
O_2, liquid form	*kg/t*	*0.00*	*0.00*	*0.05*	*0.05*	*NA*
Pitch dispergents	kg/t	0.012	0.018	0.010	0.010	NA
Polymer and retention agents	kg/t	0.047	0.582	0.233	0.233	NA
S, sulphur	kg/t	8.42	0.00	0.00	0.00	NA
Sizing agents	kg/t	0.000	0.404	0.139	0.139	NA
AKD sizer (alkyl ketene dimer)	*kg/t*	*0.00*	*0.155*	*0.100*	*0.100*	*NA*
ASA sizer (alkenyl succinic anhydride)	*kg/t*	*0.00*	*0.183*	*0.023*	*0.023*	*NA*
Rosin	*kg/t*	*0.00*	*0.065*	*0.016*	*0.016*	*NA*
SO_2, sulphur dioxide	kg/t	0.00	0.00	0.00	0.00	NA
Talc/malisul	Kg/t	0.000	0.028	0.000	0.000	NA
Urea	Kg/t	0.00	0.46	0.18	0.18	NA
Starch, corn (including modified and cationic starch from corn)	kg/t	0.00	3.14	9.40	9.40	9.69
Starch, potato (including modified and cationic starch from potat0)	kg/t	0.00	1.45	11.45	11.45	0.00
Starch, wheat (including modified and cationic starch from wheat)	kg/t	0.00	6.46	21.33	21.33	4.14
Starch, other (flour, pea, undefined)	kg/t	0.00	2.98	5.01	5.01	7.60

EMISSIONS TO AIR						
Particulates, <2.5µm	kg/t	0.0188	0.0264	0.0027	0.0027	0.00043
Particulates, >2.5µm and <10µm	kg/t	0.0104	0.0146	0.0015	0.0015	0.00026
Particulates, >10µm	kg/t	0.0554	0.0779	0.0078	0.0078	0.00023
CO_2 (fossil)	kg/t	174.25	67.19	202.52	202.52	54.86
CO_2 (biomass)	kg/t	790.74	1106.99	122.90	122.90	0.02
CO	kg/t	1.14	1.37	0.044	0.044	0.0028
NOx (as NO_2)	kg/t	0.86	0.78	0.18	0.18	0.0151
SOx (as SO_2)	kg/t	0.48	0.16	0.065	0.065	0.0096
TRS (H_2S as S)	kg/t	0.106	0.009	n/a	n/a	0.000
EMISSIONS TO WATER						
Water output	m^3/t					
Cooling water to freshwater	m^3/t	22.43	6.01	1.04	1.04	0.00
Cooling water to seawater	m^3/t	0.00	2.86	0.33	0.33	0.00
Process water to off-site wastewater treatment	m^3/t	0.00	1.74	1.00	1.00	0.15
Process water to freshwater after treatment onsite wastewater treatment	m^3/t	22.43	10.71	4.02	4.02	0.01
Process water to seawater after treatment onsite wastewater treatment	m^3/t	o.00	7.15	0.52	0.52	0.00
Total water out	*m^3/t*	*44.86*	*28.47*	*6.91*	*6.91*	*0.17*
Waterborne emissions - freshwater						
COD	kg/t	6.44	1.89	0.81	0.81	0.00
BOD5	kg/t	0.41	0.23	0.19	0.19	0.00
TOC	kg/t	4.28	0.62	0.041	0.041	0.00
Suspended solids	kg/t	0.93	0.36	0.16	0.16	0.00
Total Nitrogen	kg/t	0.875	0.044	0.046	0.046	0.00
AOX	kg/t	0.0447	0.0053	0.00048	0.00048	0.00
Total Phosphorous	kg/t	0.0157	0.0042	0.0047	0.0047	0.00
Waterborne emissions - seawater						
COD	kg/t	0.00	1.75	0.09	0.09	0.00
BOD5	kg/t	0.00	0.31	0.007	0.007	0.00
TOC	kg/t	0.00	0.26	0.018	0.018	0.00
Suspended solids	kg/t	0.00	0.29	0.013	0.013	0.00
Total Nitrogen	kg/t	0.00	0.051	0.0075	0.0075	0.000
AOX	kg/t	0.00	0.0013	0.00011	0.00011	0.000
Total Phosphorous	kg/t	0.00	0.0089	0.00042	0.00042	0.0000

RESIDUES	WET WEIGHT					
Calcium carbonate	kg/t (75% dry content)	0.491	0.00	0.069	0.069	NA
Ink residues	kg/t (50% dry content)	NA	NA	NA	NA	0.355
Inorganic ashes (10 01 01)	kg/t (85% dry content)	7.481	12.06	7.928	8.632	NA
Green liquor sludge	kg/t (32% dry content)	0.466	5.24	0.716	0.206	NA
Organic primary fibre sludge	kg/t (43% dry content)	0.495	0.015	21.247	21.247	NA
Lime mud	kg/t (32% dry content)	0.222	10.745	0.080	0.080	NA
Organic biological treatment sludge	kg/t (43% dry content)	15.984	7.470	17.543	17.543	0.336
Bark and wood	kg/t (45% dry content)	0.254	0.003	0.030	0.030	NA
Paper for recycling	kg/t (90% dry content)	NA	NA	NA	NA	120
Rejects - total	kg/t (57% dry content)	7.394	12.449	46.969	46.969	NA
Rejects, paper related**	kg/t (57% dry content)	2.462	4.145	15.641	15.641	NA
Rejects, other***	kg/t (57% dry content)	4.925	8.291	31.281	31.281	NA
Starch, glue (wet weight)	kg/t (30% dry content)	NA	NA	NA	NA	0.096
Lubricants and oil	Kg/t	0.179	0.118	0.044	0.044	0.018

«0» no input or below reporting requirements see «chemical input»
«na» not available or not measured
*As this life cycle inventory is intended to be representative of average European production, only transport from European paper mills to European corrugated board production sites has been considered in the weighted average. Transport associated with export of paper outside of Europe has not been considered
**Rejected materials that were associated with the previous use of the paper (for example, staples, paper clips, tags, adhesive labels, unrecovered fibres, etc)
***Material that is not in any way associated with the previous use of the paper (for example, foreign items such as plastic packaging, glass, sand and grit, etc)

ANNEX 2: PEER REVIEW STATEMENT

REVIEW STATEMENT ON EUROPEAN DATABASE FOR CORRUGATED BOARD LIFE CYCLE STUDIES, 2025

- Dataset owners: CEPI Containerboard & FEFCO corrugated packaging
- Dataset developer: Michael Sturges, RISE - Research Institutes of Sweden
- Reviewer: Frank Wellenreuther, ifeu - Institut for Energy and Environmental Research
- Heidelberg, April 2026

BACKGROUND AND GOAL

CEPI ContainerBoard (CCB) and the European Federation of Corrugated Board Manufacturers (FEFCO) collected data from the industry to document the environmental impact of corrugated board.

The result is a European database for life cycle studies that includes data for the production of:

- Corrugated base papers from primary fibres: Kraftliner, White Top Kraftliner and Semichemical Fluting (data from CCB)
- Corrugated base papers from recovered papers: Testliner, White Top Testliner and Wellenstoff (data from CCB)
- Corrugated board products (data from FEFCO).

The data is the twelfth edition of the database and represents averages of the inputs and outputs from the production sites per tonne paper and per tonne of corrugated board product for the year 2024.

The database report has been prepared by RISE Bioeconomy.

The updated database was presented to Frank Wellenreuther of ifeu gGmbH for critical review.

The goal of the review presented here is to ensure that:

- the methods used to compile the database are scientifically and technically valid,
- the methods are used consistently within the FEFCO LCA database,
- the data used are appropriate and reasonable in relation to the goal of the LCA Database
- the LCA database report is transparent and consistent.

REVIEW

Review procedure

This review has been commissioned by FEFCO in the context of the regular update of the FEFCO environmental database. The review work has been conducted in line with the established review procedure applied in previous database editions.

This review statement refers to the final draft version of the database report dated December 2025, covering updated data, calculations and results for the reference year 2024.

Documents provided and reviewed

The dataset developer provided the reviewer with several documents relevant for a clear understanding of the data compilation process, including:

- papermill data and calculation files for reference year 2024
- converting plant averages and calculation files
- FEFCO 2024 statistics
- FEFCO environmental database - draft report 15-12-2025.docx

The Excel sheets provided allowed the reviewer a detailed insight into the underlying data and a review of the calculation methods used.

Review of the database report

- The final draft of the database report is named FEFCO environmental database - draft report 15-12-2025. docx.
- The report contains a single European average inventory dataset covering corrugated board production including the production of the four main paper grades used.
- In an annex to the report the separate gate-to-gate inventory datasets for the four paper grades and the converting process are also included.
- It contains a very detailed section describing the production processes.
- The dataset for the corrugated board is calculated by multiplying the average paper grade composition data from the paper mills with 1.12 (as on average 1.12 tonnes of paper are used for 1 tonne corrugated box product) and adding the corrugated board data from converting facilities.
  - The detailed section describing production processes is well written and very much appreciated as it will help non-professionals to understand and therefore use this dataset correctly.
  - This calculation approach is transparently presented in the report and considered suitable for the generating of one average dataset.
- The underlying datasets differ in their representativeness. The data for Semichemical Fluting and Kraftliner represent approximately 86% of the total annual production of corrugated base papers from primary fibres in Europe. The data for the production of Testliners and Wellenstoff represent about 63% of the total annual production of corrugated base papers from recovered paper in Europe. The data on corrugated board production represents 46-50% the total annual production of corrugated board in Europe.
  - Despite slight changes in participation compared to earlier database editions, the resulting dataset is considered to be representative of the European production of corrugated board and the reference year 2024.
- Allocation of inputs and outputs was not necessary in all cases of data collection. At some sites only one grade of product is produced, at some the mills were able to assign inputs of raw materials to the different products. In remaining cases allocation between co-products has been done by data providers according to causality.
- Inputs and outputs allocated to other products (not by-products) and sold energy have been excluded from the inventory data.
- No allocation was made to by-products, so the reported inventory includes the production of these by-products.
- The allocation procedure is considered suitable to deliver the most valid results possible.
- The inventory tables include the inputs and outputs per ton net saleable product.
- The list of material inputs does not include packaging material.
- The list of material outputs includes residues.
- Total sums for some material or energy inputs are additionally presented.

- Apart from material and energy flows also transport parameters for wood, recovered paper, pulp and paper to corrugating plants are listed.
- An additional table listing internal fuels, which are not added to the inventory data as their emissions are already accounted for, is presented.
- Biogenic and fossil-based CO_2 is reported transparently.
- The reviewer appreciates the consideration of peat as fossil fuel regarding the quality of CO emissions.
- Water balances have been checked by the reviewer and are found to be sufficiently closed (the difference is also reported in the inventory).
- The inclusion of internal fuels for information purposes is appreciated.

Conclusion

The presented documentation of the dataset is considered transparent and correct, clearly describing how the dataset has been built up and what it represents in terms of production, technology, geography and time. This is considered appropriate for the intended application: gate-to-gate LCI dataset for production of corrugated board for use in LCI/LCA studies.

- the methods used to compile the database are scientifically and technically valid,
- and consistently used within the FEFCO LCA database.
- the data used are appropriate and reasonable in relation to the goal of the LCA database.
- the LCA database report is transparent and consistent.

The input and output flows have been cross-checked by the reviewer with other paper sector datasets and have been found to have a high level of completeness including all relevant flows of inputs of raw materials and energy.

Limitations

The data set refers to European industry average. This review does not apply to any individual datasets collected at single mills or corrugated board plants.

Heidelberg, 09.04.2026



Frank Wellenreuther, ifeu gGmbH

FEFCO
Corrugated Packaging

The Federation of Corrugated Board Manufacturers

Avenue Louise 250 B – 1050 Brussels
Tel + 32 2 646 40 70
www.fefco.org

CIRCULAR BY NATURE

FOLLOW US: